

Accepted Manuscript

A water-soluble supramolecular polymeric dual sensor for temperature and pH with an associated direct visible readout

Aurélie Malfait, Fanny Coumes, David Fournier, Graeme Cooke, Patrice Woisel

PII: S0014-3057(15)00108-1
DOI: <http://dx.doi.org/10.1016/j.eurpolymj.2015.02.033>
Reference: EPJ 6780

To appear in: *European Polymer Journal*

Received Date: 15 January 2015
Revised Date: 18 February 2015
Accepted Date: 19 February 2015

Please cite this article as: Malfait, A., Coumes, F., Fournier, D., Cooke, G., Woisel, P., A water-soluble supramolecular polymeric dual sensor for temperature and pH with an associated direct visible readout, *European Polymer Journal* (2015), doi: <http://dx.doi.org/10.1016/j.eurpolymj.2015.02.033>

This is a PDF file of an unedited manuscript that has been accepted for publication. As a service to our customers we are providing this early version of the manuscript. The manuscript will undergo copyediting, typesetting, and review of the resulting proof before it is published in its final form. Please note that during the production process errors may be discovered which could affect the content, and all legal disclaimers that apply to the journal pertain.



A water-soluble supramolecular polymeric dual sensor for temperature and pH with an associated direct visible readout

Aurélie Malfait,^a Fanny Coumes,^a David Fournier,^a Graeme Cooke^{b*} and Patrice Woisel^{a*}

a) Université Lille Nord de France, Unité des Matériaux Et Transformations (UMET, UMR CNRS 8207), Ingénierie des Systèmes Polymères (ISP), 59655 Villeneuve d'Ascq Cedex, France. E-mail: patrice.woisel@ensc-lille.fr

b) Glasgow Centre for Physical Organic Chemistry, WestCHEM, School of Chemistry, Joseph Black Building, University of Glasgow, Glasgow, G12 8QQ, UK. E-mail: graemec@chem.gla.ac.uk

Abstract

We report a multi-stimuli responsive polymeric sensor consisting of a pseudorotaxane-like architecture fabricated from a 1,5-diaminonaphthalene end-functionalized poly(*N*-isopropyl)acrylamide (**Napht-N-PNIPAM**) and cyclobis(paraquat-*p*-phenylene) (**CBPQT⁴⁺,4Cl⁻**). The coloured nature of the poly-pseudorotaxane provides a sensor for temperature and pH in water with an associated visible readout. To create this dual responsive polymeric sensor, a new chain transfer agent (**Napht-N-CTA**) incorporating a pH-responsive 1,5-diaminonaphthalene unit was synthesized and used for the polymerization of *N*-isopropylacrylamide *via* Reversible Addition-Fragmentation Chain Transfer (RAFT). The ability of **Napht-N-PNIPAM** to form a pseudorotaxane architecture with **CBPQT⁴⁺,4Cl⁻** in aqueous media was studied by means of UV-Vis, NMR (¹H, 2D-ROESY, DOSY) and ITC experiments. Interestingly, the pseudorotaxane architecture can be reversibly dissociated upon either heating the sample above its cloud point or protonating the nitrogen atoms of the 1,5-diaminonaphthalene-based guest unit by adjusting the pH to around 1. In both cases a dramatic colour change occurs from intense blue-green to colourless.

Introduction

Stimuli-responsive polymeric materials have attracted considerable attention and have become a much studied sub-discipline in contemporary polymer chemistry [1-6]. This burgeoning field has significantly benefitted by advances in controlled (radical) polymerizations, which has led to rapid development of novel stimuli-responsive polymers with bespoke and well-defined (macro)molecular

architectures with largely predictable physicochemical properties. The growing interest in smart polymers able to respond to different stimuli including: temperature, light, pH, ionic strength, and analyte concentration has led to the development of functional polymers with a range of new applications [7-14], including smart drug delivery systems for instance [15-17]. In addition, the last decade has provided stimuli-responsive polymers capable of sensing and responding to environmental changes or the presence of analytes. Compared to their molecular-scale brethren, macromolecular based sensors offer several advantages including improved detection sensitivity, better dispersability in aqueous media, and flexibility of processing thus facilitating their integration into viable devices.


Temperature and pH play a central role in many fields of science and engineering, and as a consequence, attention has been directed towards the design of smart polymeric systems capable of monitoring these two parameters. Usually these polymeric sensor systems incorporate reporter units which take advantage of the intrinsic responsiveness of polymers to their microenvironment such as the structural changes that accompany temperature (e.g. Lower Critical Solution Temperature, LCST) or pH changes. Although numerous responsive polymer matrices incorporating either temperature or pH sensitive fluorescent probes have been reported in literature [18-24], it is noteworthy that very few dual-fluorescent sensors capable of monitoring both temperature and pH changes have been described in literature [25]. Moreover, in comparison to fluorescence based sensors, only a limited number of absorbance-based visible polymeric sensors has been reported to date. More particularly, thermo or pH responsive polymeric sensors featuring a visible readout have largely focused upon solvatochromic dyes (e.g. mercocyanine or coumarin or rhodamine type dyes, dispersed red 1, bromothymol blue) that have been physically or covalently embedded into a thermoresponsive polymer matrix [25-32].

Recently, our group has reported a straightforward supramolecular approach to elaborate a new family of thermosensors with an associated direct visible readout [33]. This host-guest concept is based on the thermo-responsiveness of coloured complexes formed from naphthalene functionalized PNIPAM as guests and cyclobis(paraquat-*p*-phenylene) (**CBPQT⁴⁺**, **4Cl⁻**) as host, that above their cloud points undergo LCST-induced dethreading, thereby resulting in a complete disappearance of the characteristic purple colour associated with complexes of this type. This concept was notably exploited to create supramolecular-based programmable, reprogrammable thermometers that also display a thermal memory function. Here, we report on the elaboration of a new supramolecular polymeric system, consisting of a 1,5-diaminonaphthalene end functionalized PNIPAM (**Napht-N-PNIPAM**) complexed with **CBPQT⁴⁺**, **4Cl⁻**, capable of sensing both temperature and

pH with a visual readout. In this paper, the synthesis of **Napht-N-PNIPAM** and its propensity to form a strong coloured host-guest assembly in aqueous media with **CBPQT⁴⁺, 4Cl⁻** is reported in detail, as well as the thermo and pH responsiveness of **Napht-N-PNIPAM:CBPQT** supramolecular complex.

Results & Discussion

A novel RAFT agent **Napht-N-CTA** was conveniently prepared from the coupling reaction of 1,5-bis[2-(2-hydroxyethoxy)ethylamino]naphthalene[34] **1** and 2-(1-isobutyl)sulfanylthiocarbonylsulfanyl-2-methyl propionic acid (compound **2**, Scheme 1).

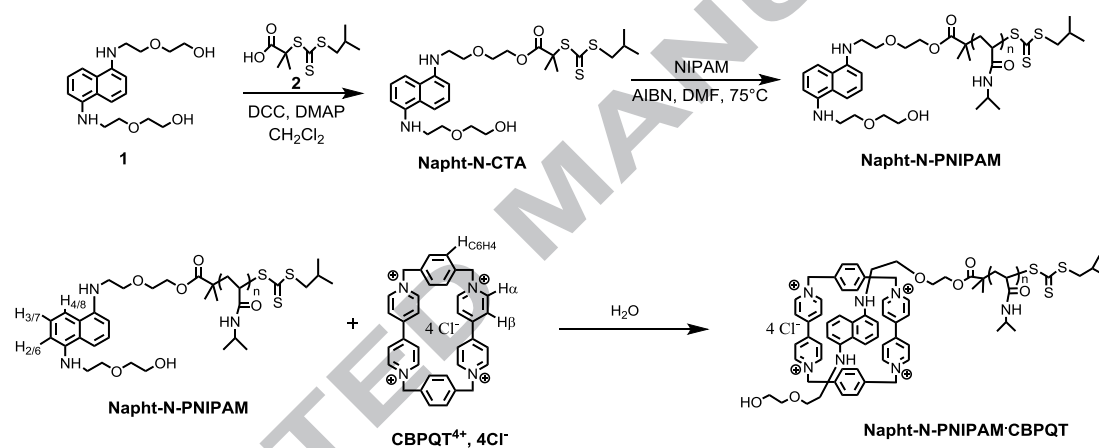

Scheme 1. Synthesis of the RAFT agent **Napht-N-CTA** and the polymer **Napht-N-PNIPAM**

The structure of the **Napht-N-CTA** was confirmed by ^1H NMR, ^{13}C NMR and 2D NMR (see ESI Figures S1, S2 and S3 respectively) spectroscopies. ^1H NMR spectrum of **Napht-N-CTA** recorded in CD_3CN revealed the presence of the characteristic signals of protons belonging to the naphthalene unit ($\delta_{\text{H}_{2/6}} = \delta_{\text{H}_{3/7}} = 7.4$ ppm and $\delta_{\text{H}_{4/8}} = 6.9$ ppm) and the methyl fragment of the isobutyl group ($\delta_{\text{CH}_3} = 0.9$ ppm). Furthermore, the ^{13}C spectrum clearly displayed chemical shifts at 172.1 ppm and 222.2 ppm ascribed to the amide carbonyl group and the thiocarbonyl fragment of the RAFT agent, respectively.

The ability of the **Napht-N-CTA** to promote RAFT polymerizations was demonstrated with *N*-isopropylacrylamide (NIPAM). The polymerization of NIPAM (150 equiv.) was carried out with azobis(isobutyronitrile) (AIBN, 0.2 equiv.) as a radical source and **Napht-N-CTA** (1 equiv.) in DMF at 75°C for 1h. The absolute molecular weight and the dispersity index (\mathcal{D}) of the polymer were determined by SEC ($M_{n,\text{abs}} = 14810$ g/mol, $\mathcal{D} = 1.07$, $dn/dc = 0.0886$ mL/g, Figure S 4). In addition, the structure of **Napht-N-PNIPAM** was confirmed by ^1H NMR spectroscopy in D_2O , which displayed the

characteristic signals of PNIPAM ($\delta_{\text{N-CH}} = 3.95$ ppm, $\delta_{\text{CH}_3} = 1.20$ ppm, Figure S 5) in addition to those belonging to the naphthalene moiety ($\delta_{\text{H}_{2/6}} = \delta_{\text{H}_{3/7}} = 7.5$ ppm, $\delta_{\text{H}_{4/8}} = 6.9$ ppm, Figure 1a).

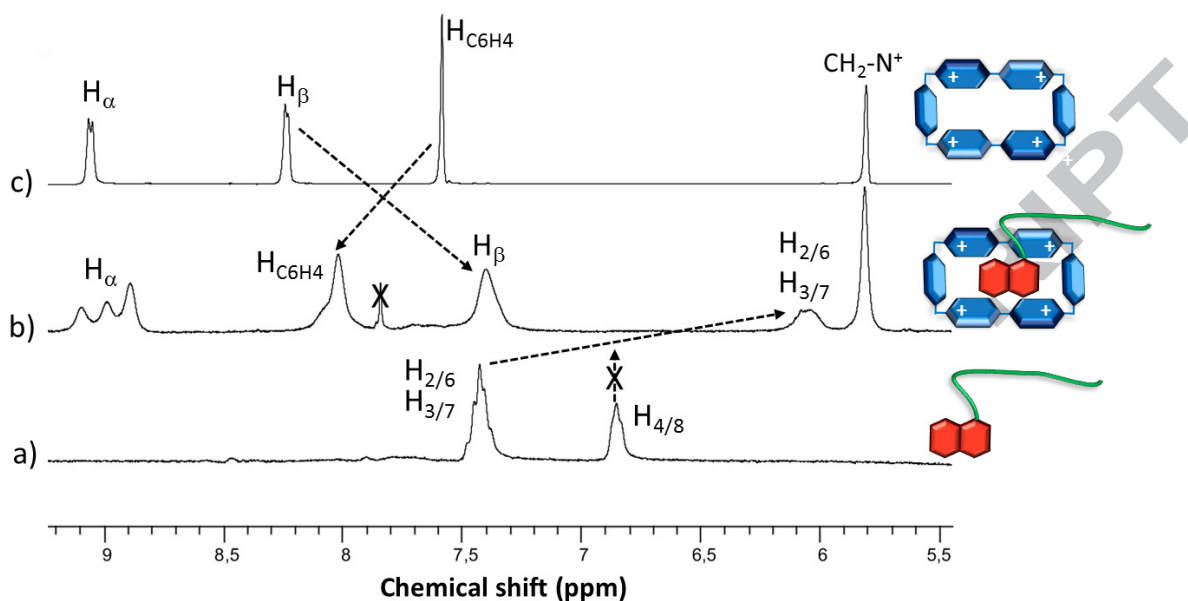


Figure 1. Partial ^1H NMR spectra of: a) Napht-N-PNIPAM, b) Napht-N-PNIPAM/CBPQT and c) $\text{CBPQT}^{4+}, 4\text{Cl}^-$. Recorded at 18°C in D_2O .

Next, the ability of electron-rich **Napht-N-PNIPAM** to form a 1:1 complex with the electron-deficient $\text{CBPQT}^{4+}, 4\text{Cl}^-$ was investigated. The addition of aliquots of $\text{CBPQT}^{4+}, 4\text{Cl}^-$ to a solution of **Napht-N-PNIPAM** in water resulted in the immediate appearance of an intense blue-green colour, which is consistent with the formation of a donor-acceptor complex between the π -electron rich **Napht-N-PNIPAM** and the π -electron deficient $\text{CBPQT}^{4+}, 4\text{Cl}^-$. This observation was confirmed by the appearance of a band centered at 697 nm in its UV-vis spectrum (Figure 2a).

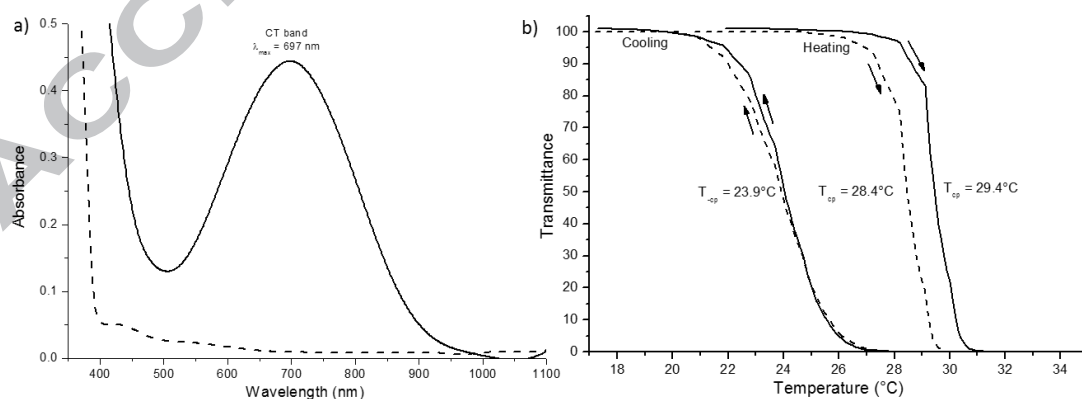


Figure 2. UV-vis spectra (a) and thermo-sensitive phase transition recorded at 950 nm (b) of Napht-N-PNIPAM (---) and Napht-N-PNIPAM in presence of 1 equivalent of CBPQT^{4+} (—).

Next, we have studied the complex formation between **Napht-N-PNIPAM** and **CBPQT⁴⁺, 4Cl⁻** in aqueous media by using NMR spectroscopy (¹H, 2D-ROESY, DOSY, COSY). The ¹H NMR spectrum of a 1:1 mixture **Napht-N-PNIPAM** and **CBPQT⁴⁺, 4Cl⁻** revealed significant shifts for the H_β ($\Delta\delta = -0.96$ ppm), H_{C6H4} ($\Delta\delta = +0.31$ ppm) protons of **CBPQT⁴⁺, 4Cl⁻** and H_{2/6}, H_{3/7} ($\Delta\delta = -1.38$ ppm), H_{4/8} ($\Delta\delta = -5.7$ ppm) of **Napht-N-PNIPAM** (Figure 1b), that is in good agreement with previously reported data for complexes of this type. [34]

¹H NMR titration experiments were also carried out on **Napht-N-PNIPAM** upon adding aliquots of **CBPQT⁴⁺, 4Cl⁻** (Figure S 6). ¹H NMR spectra clearly indicated the existence of the signal for uncomplexed H_{4/8} protons upon the addition of aliquots of **CBPQT⁴⁺, 4Cl⁻**, thereby suggesting a slow exchange at the NMR timescale between the uncomplexed and complexed forms. Moreover, the ¹H NMR titration revealed the complete disappearance of the signal of uncomplexed H_{4/8} protons at 6.9 ppm when 1 equiv. of **CBPQT⁴⁺, 4Cl⁻** was added, thus indicating the formation of a 1:1 complex between **Napht-N-PNIPAM** and **CBPQT⁴⁺, 4Cl⁻**. Further proof regarding the formation of a pseudorotaxane architecture between **Napht-N-PNIPAM** and **CBPQT⁴⁺, 4Cl⁻** was also obtained from its 2D ROESY spectrum that indeed displayed a dipolar correlation between H_{2/6}, H_{3/7} and H_{C6H4} protons belonging to the guest and host partners, respectively (Figure 3a).

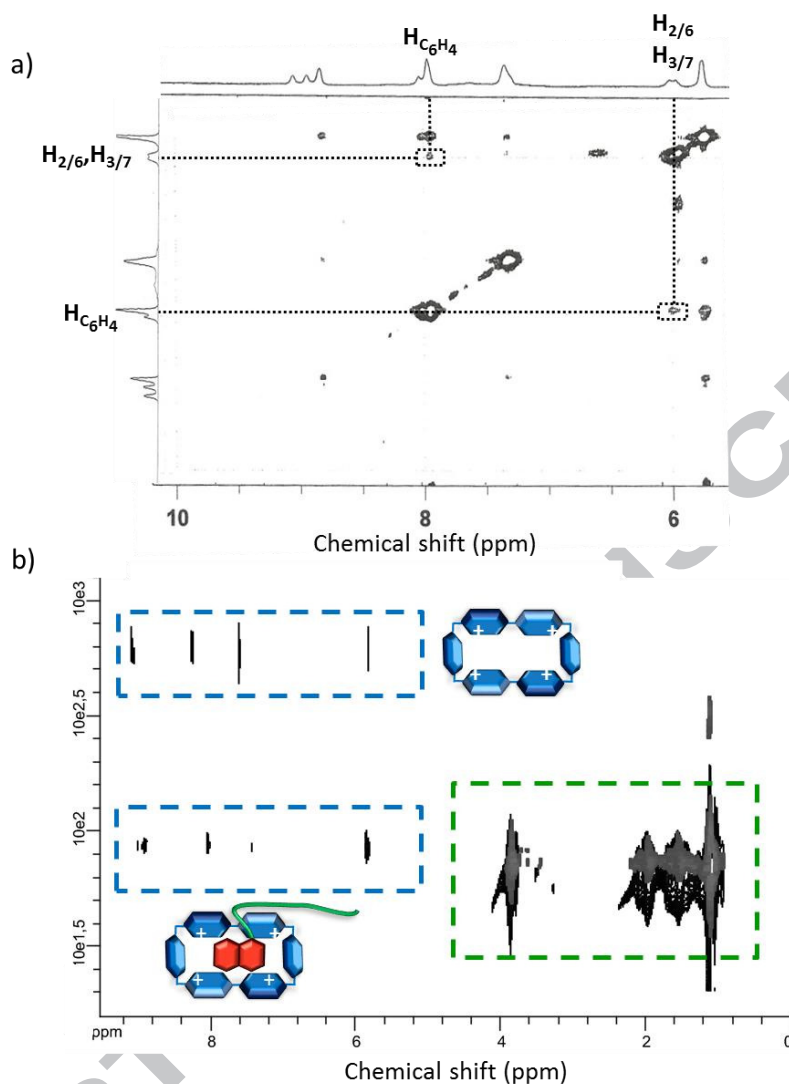


Figure 3. a) 2D-ROESY ^1H - ^1H spectrum (D_2O) of Napht-N-PNIPAM/CBPQT, b) Superimposed ^1H NMR DOSY (D_2O) experiments of free CBPQT^{4+} , 4Cl^- (upper black spectrum), Napht-N-PNIPAM (grey spectrum) and the 1:1 complex Napht-N-PNIPAM/CBPQT (bottom black spectrum)

Next, to demonstrate the robustness of the host-guest interaction between **Napht-N-PNIPAM** and CBPQT^{4+} , 4Cl^- , two-dimensional diffusion ordered spectroscopy (DOSY) ^1H NMR spectroscopy and isothermal titration microcalorimetry (ITC) experiments were undertaken. 2D-DOSY ^1H NMR spectroscopy experiments showed for solutions of their individual components (CBPQT^{4+} , 4Cl^- and **Napht-N-PNIPAM**) have a diffusion coefficient value of $1585 \mu\text{m}^2 \text{s}^{-1}$ and $73.3 \mu\text{m}^2 \text{s}^{-1}$, respectively (Figure 3b). When DOSY experiments were undertaken on 1:1 **Napht-N-PNIPAM**/ CBPQT^{4+} , 4Cl^- solution of the complex, the protons belonging to CBPQT^{4+} , 4Cl^- moved to a lower and identical diffusion coefficient to that of **Napht-N-PNIPAM** ($73.3 \mu\text{m}^2 \text{s}^{-1}$). Moreover, no signals for the free CBPQT^{4+} , 4Cl^- were observed, thus confirming the efficiency of the coupling between CBPQT^{4+} , 4Cl^- and **Napht-N-PNIPAM**. In addition, ITC experiments indicated that addition of aliquots of CBPQT^{4+} , 4Cl^- to a dilute solution of **Napht-N-PNIPAM** in water gave rise to a large exothermic response ($\Delta H = -46.08 (\pm 0.26)$)

kcal/mol) in good agreement with the relatively large estimated association constant of $K_a = 9.2 (\pm 0.7) \times 10^4 \text{ M}^{-1}$ (Figure S 7).

Thermo-responsiveness of Napht-N-PNIPAM'CBPQT complex in water

The thermoresponsiveness of the **Napht-N-PNIPAM'CBPQT** complex was first investigated by turbidity measurements using UV-vis spectroscopy (Figure 2b). The cloud point of the polymer complexed with **CBPQT⁴⁺, 4Cl⁻** in water was determined as 29.4°C from the midpoint of the transmittance value (Figure 2b). This value was slightly higher than the cloud point estimated for **Napht-N-PNIPAM** ($T_{cp} = 28.4^\circ\text{C}$, Figure 2b), thereby indicating that the hydrophilicity-hydrophobicity balance of the material can be displaced toward a more hydrophilic structure by masking the hydrophobicity of the naphthalene unit through the formation of a pseudorotaxane-like architecture with the more hydrophilic **CBPQT⁴⁺, 4Cl⁻** host [10]. More interestingly, despite the high K_a value, the phase transition of the complex ($T > T_{cp}$) induced a complete disappearance of the green-blue colour of the aqueous solution, suggesting a disruption of the complex upon crossing the T_{cp} . This was also evidenced by the fact that the UV-vis spectra of **Napht-N-PNIPAM** and **Napht-N-PNIPAM'CBPQT, 4Cl⁻** were quite similar upon cooling the samples (Figure 2b). To get further insight on the cloud point-mediated host-guest disassembly, variable temperature ¹H NMR spectroscopy experiments were carried out. More particularly, we have investigated the changes in the ¹H NMR spectra of **Napht-N-PNIPAM'CBPQT** complex upon cycling the temperature between 18°C ($T < T_{cp}$) and 35°C ($T > T_{cp}$) in D₂O. As expected, the ¹H NMR spectra of **Napht-N-PNIPAM'CBPQT** upon heating from 18°C (Figure 4a) to 35°C (Figure 4b) revealed a complete disappearance of the protons belonging to the polymer due to the precipitation of the polymer at 35°C ($T > T_{cp}$). Moreover, the signals recorded at 35°C on Figure 4b perfectly fit to the signal of the protons of uncomplexed **CBPQT⁴⁺** (Figure 4c), clearly suggesting that the dethreading of the complexation occurred upon heating the complex over the cloud point. In addition, when the temperature was cooled below the cloud point, the colour of the solution turned back to intense blue-green. This feature was monitored by UV-vis spectroscopy and it appeared that the maximum of absorbance of the absorption at 697 nm did not change even after 3 cycles of heating/cooling cycles, suggesting that the complexation/dethreading upon simply heating and cooling the aqueous solution is reversible (Figure S 8).


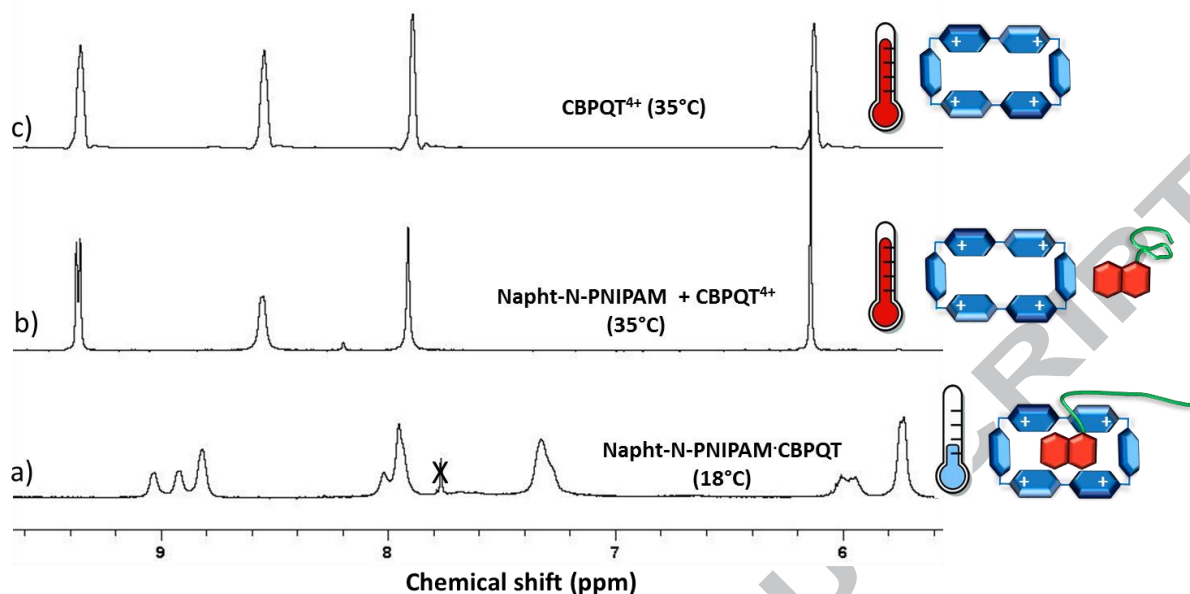


Figure 4. Partial ^1H NMR spectra (D_2O) of $\text{Napht-N-PNIPAM}\cdot\text{CBPQT}$ at a) 18°C , b) 35°C and c) $\text{CBPQT}^{4+}, 4\text{Cl}^-$ at 35°C .

pH-responsiveness of $\text{Napht-N-PNIPAM}\cdot\text{CBPQT}$ complex in water

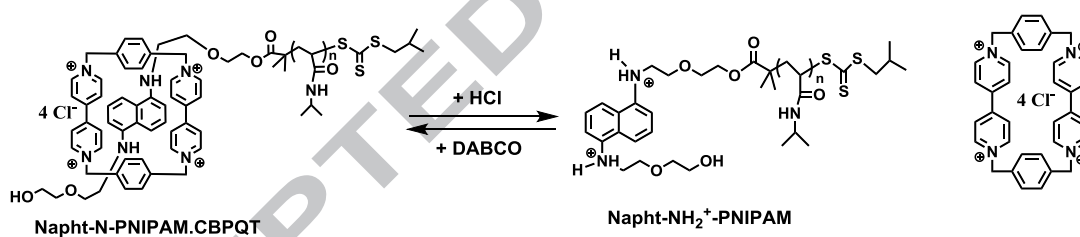

Scheme 2. Study of the pH-responsiveness of Napht-N-PNIPAM

After demonstrating the thermo-sensitivity of $\text{Napht-N-PNIPAM}\cdot\text{CBPQT}$, its pH-responsiveness was next studied (Scheme 2). Here, the main objective was to exploit the propensity of the diammononaphthalene unit located on PNIPAM to become protonated in acidic environments, thus affording the corresponding $\text{Napht-NH}_2^+\text{-PNIPAM}$ to promote the dethreading of the pseudorotaxane architecture through Coulombic repulsion. Upon the addition of aliquots of aqueous HCl to a solution containing the $\text{Napht-N-PNIPAM}\cdot\text{CBPQT}$ complex, the intense green colour ($\lambda_{\text{max}} = 697 \text{ nm}$) disappeared rapidly and a colourless solution was observed as depicted in Figure 5. The UV spectrum upon adding HCl was almost identical to that of the uncomplexed polymer. Moreover, the reversibility of the procedure was demonstrated by adding aliquots of aqueous basic solution of 1,4-diazabicyclo[2.2.2]octane (DABCO, 1.5M in H_2O) until $\text{pH} = 7$ was reached. In this way, the colour of

the solution turned from colourless to intense blue-green and the obtained UV spectrum showed the characteristic band at 697 nm (Figure S 9). It is noteworthy that performing 3 complete cycles of pH = 1/pH = 7 switching provided evidence for successive decomplexation /complexation (Figure S 9).

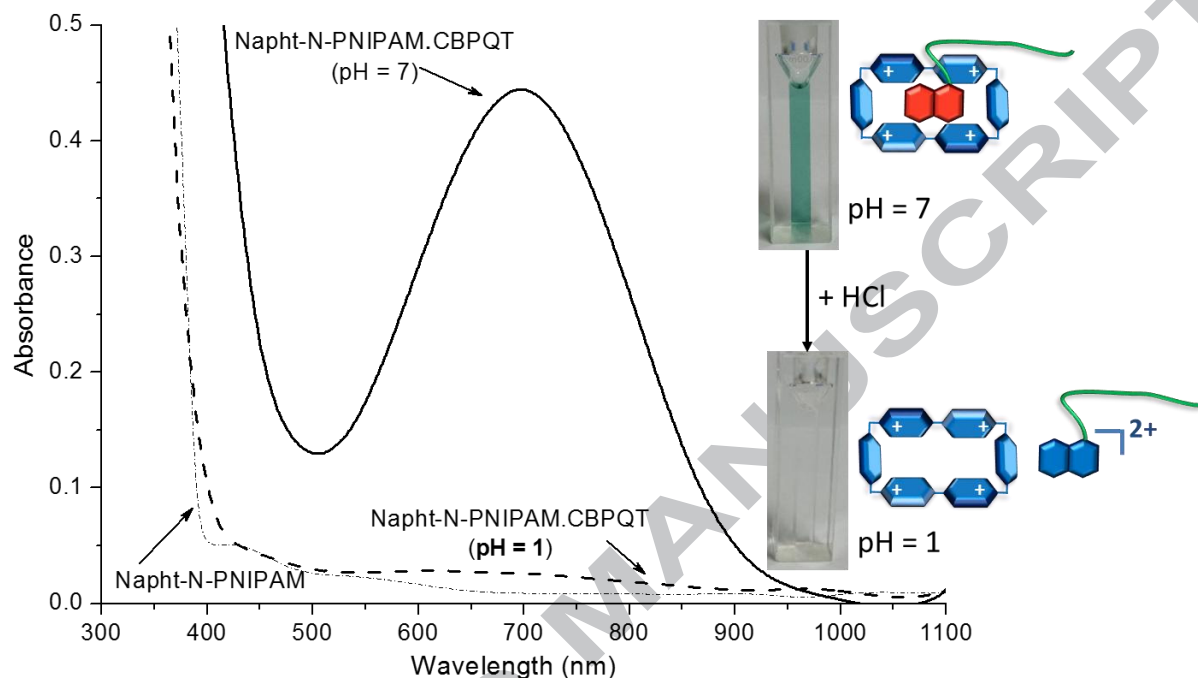


Figure 5. UV-vis spectra of uncomplexed Napht-N-PNIPAM and Napht-N-PNIPAM in presence of 1 equiv. of CBPQT^{4+} , 4Cl^- at pH = 1 and pH = 7

In addition to UV-vis investigations, ^1H NMR spectroscopy experiments were performed to corroborate optical studies in acidic medium. As shown on Figure 6, when aliquots of DCI (35 wt% in D_2O) were added to the $\text{Napht-N-PNIPAM}\cdot\text{CBPQT}^{4+}$ complex (spectrum b), signals corresponding to the protons of uncomplexed CBPQT^{4+} , 4Cl^- were observed (*i.e.* H_α , H_β , $\text{H}_{\text{C}_6\text{H}_4}$), indicating that the protonation of the naphthalene unit efficiently led to the disruption of the host/guest complex upon decreasing the pH of the solution.

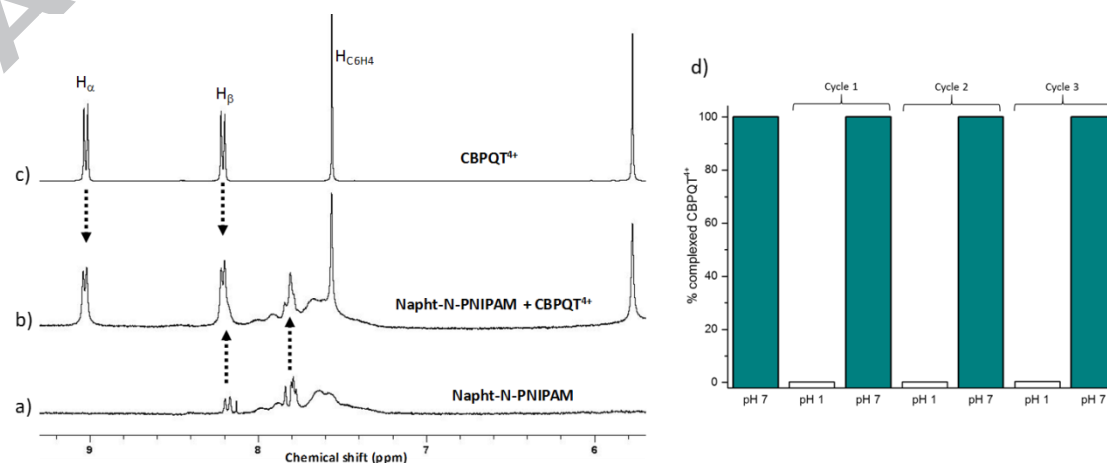


Figure 6. Partial ^1H NMR spectra (35%wt DCl in D_2O) of a) Napht- NH_2^+ -PNIPAM, b) polymer complex in acidic medium and c) CBPQT^{4+} , 4 Cl^- . Chart d) represents the reversibility of pH = 7/pH = 1 switching process upon the addition of DCl (35%wt in D_2O) and DABCO (1.5M in D_2O) showing the complexation/dethreading phenomena.

The reversibility of the procedure was demonstrated by adding aliquots of an aqueous solution of DABCO (1.5M in D_2O) until pH = 7 was reached. As stated previously, the colour of the solution turned intense blue-green when the pH was adjusted to 7. In the ^1H NMR spectrum (Figure S 10), the signals of the protons of free CBPQT^{4+} disappeared while characteristic signals resulting from host-guest complexation appeared. Moreover, the reversibility of the procedure was demonstrated by performing 3 complete pH = 1/pH = 7 cycles by simply adding aliquots of solutions of DCl and DABCO, respectively. The resulting ^1H NMR spectra (Figure S 10) clearly demonstrate the reversibility of the experiment and the stability of the species after several cycles.

Conclusion

In this contribution, we have synthesized, using a RAFT procedure, a novel well-defined thermoresponsive polymer (Napht-N-PNIPAM) bearing a pH-sensitive 1,5-diaminonaphthalene moiety. We have demonstrated its ability to form a strong coloured Napht-N-PNIPAM· CBPQT^{4+} based pseudorotaxane-like architecture in water with CBPQT^{4+} , 4 Cl^- by performing ^1H NMR spectroscopy, ITC and UV-Vis measurements. Interestingly, this complex can be conveniently disassembled either beyond its cloud point or in acidic conditions, thereby leading in both cases to the visual disappearance of the intense blue-green solution. Hence, such supramolecular assemblies can be considered as a dual sensor capable to sense both temperature and pH with a direct visible readout. Based on this supramolecular approach, we are currently designing more sophisticated multifunctional sensors capable of monitoring temperature, pH and CO_2 . Our work in this area will be reported in due course.

Acknowledgments

P.W. gratefully acknowledges financial support from the Agence Nationale de la Recherche (STRAPA project, ANR-12-BS08-0005). GC thanks the EPSRC for funding (EP/E036244). The authors would thank Marc Bria for his help and fruitful discussions about NMR experiments.

References

- [1] Mendes PM. Stimuli-responsive surfaces for bio-applications. *Chem Soc Rev.* 2008;37(11):2512-2529.
- [2] Roy D, Cambre JN, Sumerlin BS. Future perspectives and recent advances in stimuli-responsive materials. *Prog Polym Sci.* 2010;35(1–2):278-301.
- [3] Liu F, Urban MW. Recent advances and challenges in designing stimuli-responsive polymers. *Prog Polym Sci.* 2010;35(1–2):3-23.
- [4] Hoffman AS. Stimuli-responsive polymers: Biomedical applications and challenges for clinical translation. *Adv Drug Delivery Rev.* 2013;65(1):10-16.
- [5] Zhuang J, Gordon MR, Ventura J, Li L, Thayumanavan S. Multi-stimuli responsive macromolecules and their assemblies. *Chem Soc Rev.* 2013;42(17):7421-7435.
- [6] Schattling P, Jochum FD, Theato P. Multi-stimuli responsive polymers - the all-in-one talents. *Polym Chem.* 2014;5(1):25-36.
- [7] Cooke G, Garety JF, Hewage SG, Jordan BJ, Rabani G, Rotello VM, et al. Tuneable Side-Chain Supramolecular Polymer. *Org Lett.* 2007;9(3):481-484.
- [8] Bigot J, Bria M, Caldwell ST, Cazaux F, Cooper A, Charleux B, et al. LCST: a powerful tool to control complexation between a dialkoxynaphthalene-functionalised poly(N-isopropylacrylamide) and CBPQT4⁺ in water. *Chem Commun.* 2009(35):5266-5268.
- [9] Stuart MAC, Huck WTS, Genzer J, Muller M, Ober C, Stamm M, et al. Emerging applications of stimuli-responsive polymer materials. *Nat Mater.* 2010;9(2):101-113.
- [10] Sambe L, Stoffelbach F, Lyskawa J, Delattre F, Fournier D, Bouteiller L, et al. Host–Guest Modulation of the Micellization of a Tetrathiafulvalene-Functionalized Poly(N-isopropylacrylamide). *Macromolecules.* 2011;44(16):6532-6538.
- [11] Cabane E, Zhang X, Langowska K, Palivan CG, Meier W. Stimuli-Responsive Polymers and Their Applications in Nanomedicine. *Biointerphases.* 2012;7(1).
- [12] Kelley EG, Albert JNL, Sullivan MO, Epps III TH. Stimuli-responsive copolymer solution and surface assemblies for biomedical applications. *Chem Soc Rev.* 2013;42(17):7057-7071.
- [13] Ge Z, Liu S. Functional block copolymer assemblies responsive to tumor and intracellular microenvironments for site-specific drug delivery and enhanced imaging performance. *Chem Soc Rev.* 2013;42(17):7289-7325.
- [14] Doring A, Birnbaum W, Kuckling D. Responsive hydrogels - structurally and dimensionally optimized smart frameworks for applications in catalysis, micro-system technology and material science. *Chem Soc Rev.* 2013;42(17):7391-7420.
- [15] Klaikherd A, Nagamani C, Thayumanavan S. Multi-Stimuli Sensitive Amphiphilic Block Copolymer Assemblies. *J Am Chem Soc.* 2009;131(13):4830-4838.
- [16] Motornov M, Roiter Y, Tokarev I, Minko S. Stimuli-responsive nanoparticles, nanogels and capsules for integrated multifunctional intelligent systems. *Prog Polym Sci.* 2010;35(1–2):174-211.
- [17] Mura S, Nicolas J, Couvreur P. Stimuli-responsive nanocarriers for drug delivery. *Nat Mater.* 2013;12(11):991-1003.
- [18] Gota C, Uchiyama S, Ohwada T. Accurate fluorescent polymeric thermometers containing an ionic component. *Analyst.* 2007;132(2):121-126.
- [19] Shiraishi Y, Miyamoto R, Hirai T. A Hemicyanine-Conjugated Copolymer as a Highly Sensitive Fluorescent Thermometer. *Langmuir.* 2008;24(8):4273-4279.
- [20] Pietsch C, Vollrath A, Hoogenboom R, Schubert US. A Fluorescent Thermometer Based on a Pyrene-Labeled Thermoresponsive Polymer. *Sensors.* 2010;10(9):7979-7990.
- [21] Pietsch C, Schubert US, Hoogenboom R. Aqueous polymeric sensors based on temperature-induced polymer phase transitions and solvatochromic dyes. *Chem Commun.* 2011;47(31):8750-8765.

- [22] Okabe K, Inada N, Gota C, Harada Y, Funatsu T, Uchiyama S. Intracellular temperature mapping with a fluorescent polymeric thermometer and fluorescence lifetime imaging microscopy. *Nat Commun.* 2012;3:705.
- [23] Wang X-d, Wolfbeis OS, Meier RJ. Luminescent probes and sensors for temperature. *Chem Soc Rev.* 2013;42(19):7834-7869.
- [24] Tsuji T, Yoshida S, Yoshida A, Uchiyama S. Cationic Fluorescent Polymeric Thermometers with the Ability to Enter Yeast and Mammalian Cells for Practical Intracellular Temperature Measurements. *Anal Chem.* 2013;85(20):9815-9823.
- [25] Pietsch C, Hoogenboom R, Schubert US. Soluble Polymeric Dual Sensor for Temperature and pH Value. *Angew Chem.* 2009;48(31):5653-5656.
- [26] Hong SW, Ahn C-H, Huh J, Jo WH. Synthesis of a PEGylated Polymeric pH Sensor and Its pH Sensitivity by Fluorescence Resonance Energy Transfer. *Macromolecules.* 2006;39(22):7694-7700.
- [27] Bryleva EY, Vodolazkaya NA, Mchedlov-Petrosyan NO, Samokhina LV, Matveevskaya NA, Tolmachev AV. Interfacial properties of cetyltrimethylammonium-coated SiO₂ nanoparticles in aqueous media as studied by using different indicator dyes. *J Colloid Interface Sci.* 2007;316(2):712-722.
- [28] Koopmans C, Ritter H. Color Change of N-Isopropylacrylamide Copolymer Bearing Reichardt's Dye as Optical Sensor for Lower Critical Solution Temperature and for Host-Guest Interaction with β -Cyclodextrin. *J Am Chem Soc.* 2007;129(12):3502-3503.
- [29] Wu W, Zhou T, Aiello M, Zhou S. Optically pH and H₂O₂ Dual Responsive Composite Colloids through the Directed Assembly of Organic Dyes on Responsive Microgels. *Chem Mater.* 2009;21(20):4905-4913.
- [30] Peng H-s, Stolwijk JA, Sun L-N, Wegener J, Wolfbeis OS. A Nanogel for Ratiometric Fluorescent Sensing of Intracellular pH Values. *Angew Chem.* 2010;49(25):4246-4249.
- [31] Li C, Zhang Y, Hu J, Cheng J, Liu S. Reversible Three-State Switching of Multicolor Fluorescence Emission by Multiple Stimuli Modulated FRET Processes within Thermoresponsive Polymeric Micelles. *Angew Chem.* 2010;49(30):5120-5124.
- [32] Pietsch C, Hoogenboom R, Schubert US. PMMA based soluble polymeric temperature sensors based on UCST transition and solvatochromic dyes. *Polym Chem.* 2010;1(7):1005-1008.
- [33] Sambe L, de La Rosa VR, Belal K, Stoffelbach F, Lyskawa J, Delattre F, et al. Programmable Polymer-Based Supramolecular Temperature Sensor with a Memory Function. *Angew Chem.* 2014;53(20):5044-5048.
- [34] Sue C-H, Basu S, Fahrenbach AC, Shveyd AK, Dey SK, Botros YY, et al. Enabling tetracationic cyclophane production by trading templates. *Chem Sci.* 2010;1(1):119-125.


Supporting Information.

Materials. All reagents were purchased from Sigma-Aldrich and used without further purification unless otherwise noted. *N*-Isopropylacrylamide (NIPAM) and azobis(isobutyronitrile) (AIBN) were recrystallized from hexane and methanol, respectively. 1,5-bis[2-(2-hydroxyethoxy)ethylamino]naphthalene[1] (compound **1**), 2-(1-isobutyl)sulfanylthiocarbonylsulfanyl-2-methylpropionic acid[2] (compound **2**) were synthesized according to the procedure described in literature.

Analytical Techniques. ^1H NMR and ^{13}C spectra were recorded with a Bruker Advance 300 or 400 MHz spectrometer. Polymers were analyzed by size exclusion chromatography in THF at 40 °C with a flow rate of 1 mL/min and a polymer concentration of 3 mg/mL after filtration through a 0.45 μm pore-size membrane. SEC measurements were performed on a Waters system equipped with three columns (Styragel HR1, Styragel HR3, Styragel HR4) placed in series and coupled with two Wyatt detectors: a differential refractive index (RI) detector, and a Multi Angle Light Scattering (MALS) detector (laser $\lambda = 670$ nm). The absolute number-average molar masses were calculated from combined LS and RI signals with the Astra software, using an average refractive index increment (dn/dC) of 0.0886 mL/g for Napht-N-PNIPAM. The dn/dC was measured with the RI detector by injecting polymer solutions at six different concentrations. Isothermal titration calorimetry (ITC) experiments were performed at 15 °C using a nano-ITC titration calorimeter from TA Instruments. A 250 μL injection syringe was used with stirring at 400 rpm. Samples were dissolved in deionised water and the solutions were gently degassed under vacuum before use. Each titration comprised an initial 1 μL pre-injection followed by 24 x 10 μL injections of $\text{CBPQT}^{4+}, 4\text{Cl}^-$ (10.18 mM) into a solution of Napht-N-PNIPAM (1.21 mM). Control experiments with identical injections of $\text{CBPQT}^{4+}, 4\text{Cl}^-$ into water alone were used to correct titration data. UV/vis measurements were carried out on a Agilent UV-vis spectrophotometer equipped with a temperature controller. For cloud point measurements (concentration of polymer of 3mg/mL), spectra were recorded at 950 nm with a cooling/heating rate of 1°C/min and cloud point values were determined at 50% transmittance. Full UV-spectra were recorded at 20°C (concentration of polymer of 10mg/mL).

Synthesis of Napht-N-CTA. A solution of 1,5-bis[2-(2-hydroxyethoxy)ethylamino]naphthalene **1** (1.00g, 2.99mmol), 2-(1-isobutyl)sulfanylthiocarbonylsulfanyl-2-methylpropionic acid **2** (0.893g, 3.59mmol), DCC (0.74g, 3.59mmol) and DMAP (40mg, 0.33mmol) in dry DCM (80 mL) was stirred for 1 h at 0°C under nitrogen then at room temperature for 24h. After removal of the solid by filtration,

the solvent was evaporated to afford a crude product which was subjected to column chromatography (SiO₂: petroleum spirit / ethyl acetate 3:2). The fractions containing the product were combined and the eluent was removed in vacuum, affording the product CTA agent as brownish oil. Yield: 36 %

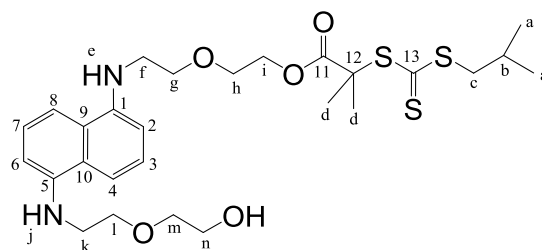

¹H NMR (300 MHz, CD₃CN), δ (ppm from TMS): 0.95 (d, *J* = 6.56 Hz, 6H, H_a), 1.69 (s, 6H, H_d), 1.91 (m, *J* = 6.57 Hz, 1H, H_b), 3.19 (d, *J* = 6.74 Hz, 2H, H_c), 3.44 (m, 4H, H_{f,k}), 3.60 (m, 2H, H_m), 3.66 (m, 2H, H_n), 3.72 (m, 2H, H_h), 3.81 (m, 4H, H_{l,g}), 4.26 (m, 2H, H_i), 5.00 (br, 2H, H_{e,j}), 6.65 (t, 2H, H_{4/8}), 7.26 (d, 2H, H_{2/6}), 7.31 (t, 2H, H_{3/7}).

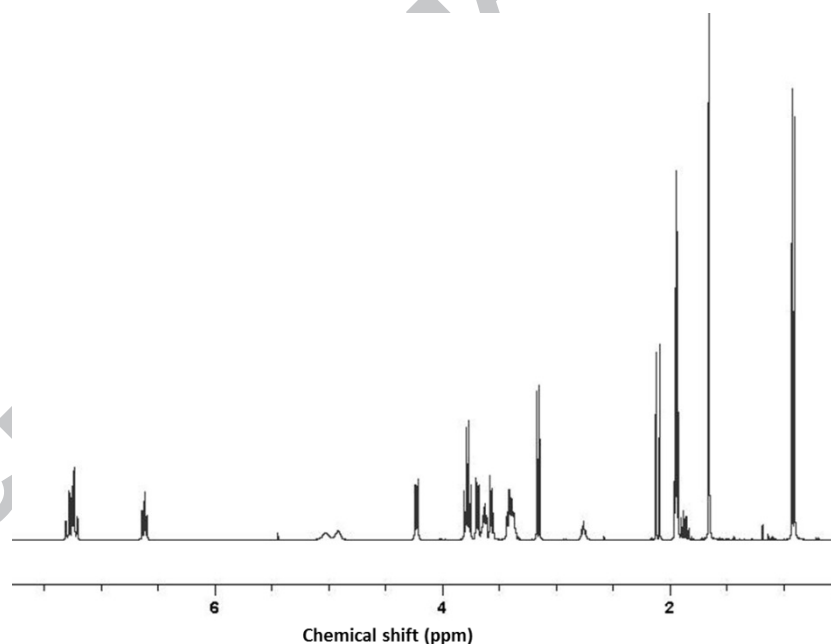


Figure S 1. ¹H NMR (CD₃CN) spectrum of Napht-N-CTA

¹³C NMR (75 MHz, CD₃CN), δ: 20.7 (C_a), 24.4 (C_d), 27.5 (C_b), 43.2 (C_{k/f}), 44.5 (C_c), 55.7 (C₁₂), 60.7 (C_i), 64.8 (C_h), 68.2 (C_n), 68.7 (C_{g/l}), 71.9 (C_m), 103.9 (C_{2/6}), 108.8 (C_{4/8}), 123.8 (C_{9,10}), 125 (C_{3/7}), 143.9 (C_{1/5}), 172.1 (C₁₁), 222.2 (C₁₃).

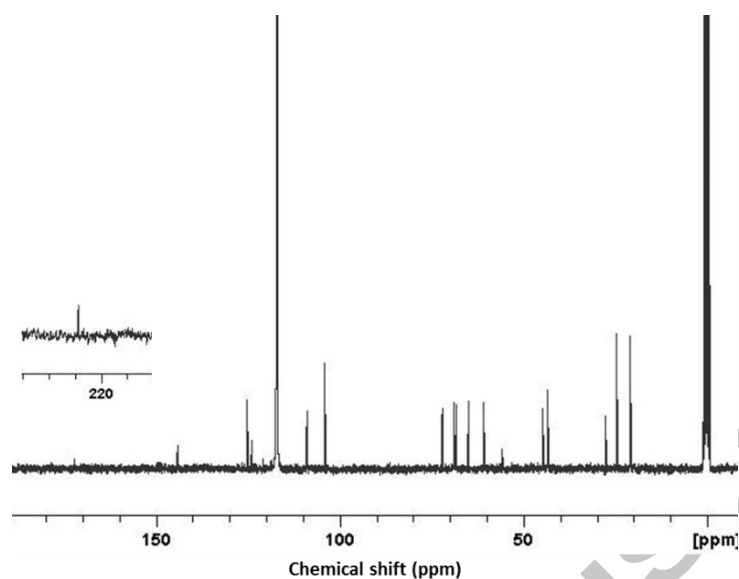


Figure S 2. ^{13}C NMR (CD_3CN) spectrum of Napht-N-CTA

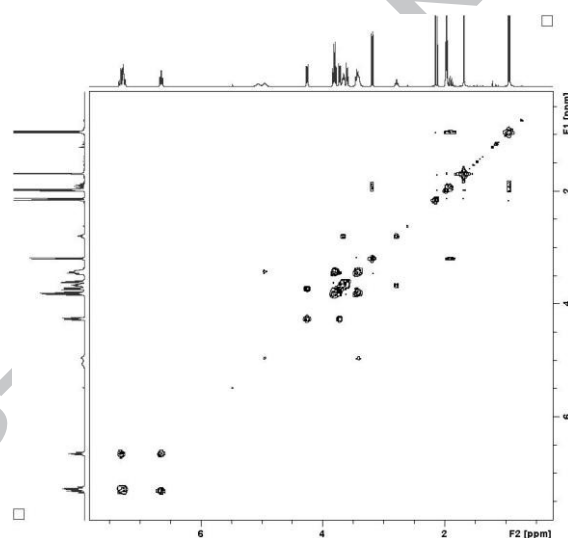


Figure S 3. COSY(^1H - ^1H) NMR spectrum of Napht-N-CTA (CD_3CN)

Synthesis of Napht-N-PNIPAM using RAFT polymerization. In a Schlenk tube were added *N*-isopropylacrylamide (2.25g, 19.81mmol), AIBN (4.4mg, 0.026mmol) and Napht-N-CTA (75mg, 0.132mmol) in DMF (5mL). The mixture was deoxygenated by nitrogen bubbling for 1h. The mixture was then heated to 75°C. After 1 hour, the final polymer Napht-N-PNIPAM was recovered by precipitation in diethyl ether. After filtration, the product was dried under vacuum until constant weight. NMR conversion = 70 %, $M_{n,abs} = 14810$ g/mol, $D = 1.07$ ($dn/dc = 0.0886$ mL/g in THF).

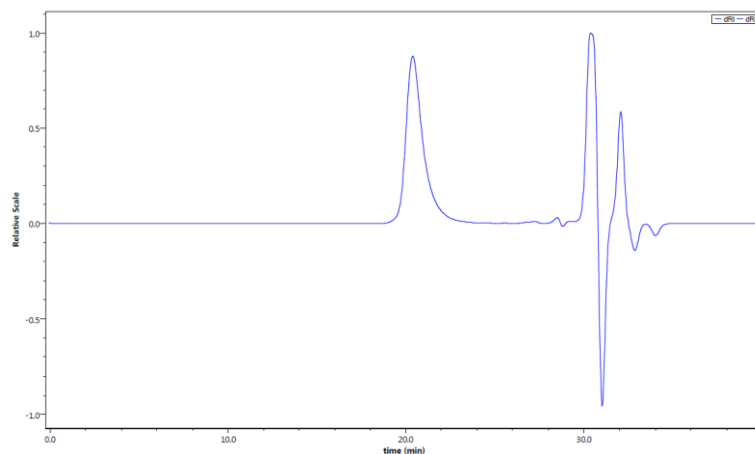


Figure S 4. GPC trace (THF) of Napht-N-PNIPAM

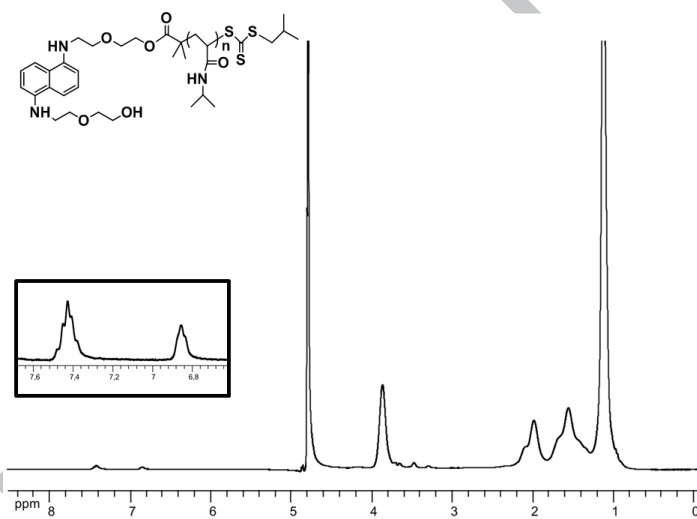
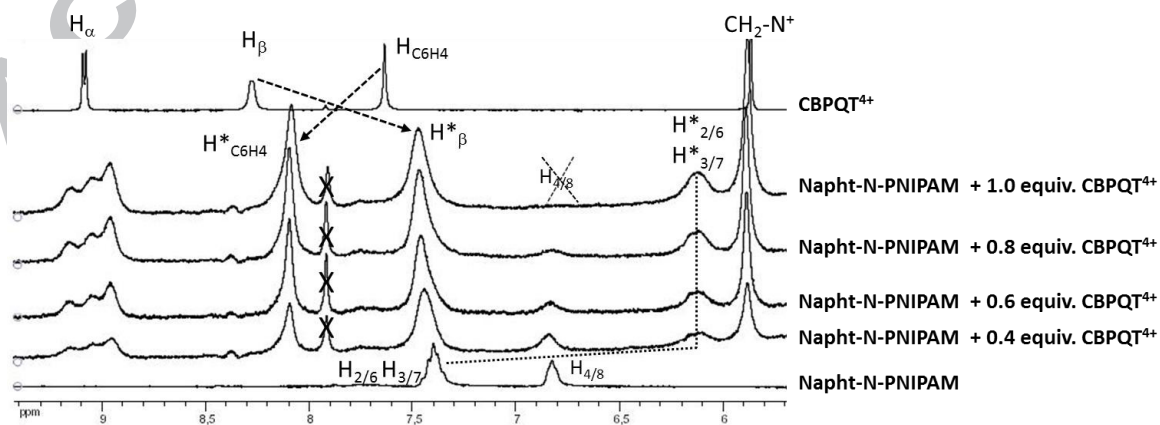
Figure S 5. ^1H NMR (D_2O) spectrum of Napht-N-PNIPAM

Figure S 6. ^1H NMR (D_2O) titration of Napht-N-PNIPAM upon the addition of aliquots of CBPQT^{4+} , 4Cl^- in D_2O . Protons marked with * correspond to protons complexed in the host/guest supramolecular assembly (The symbol X at 7.9 ppm corresponds to remaining DMF in the analyzed samples)

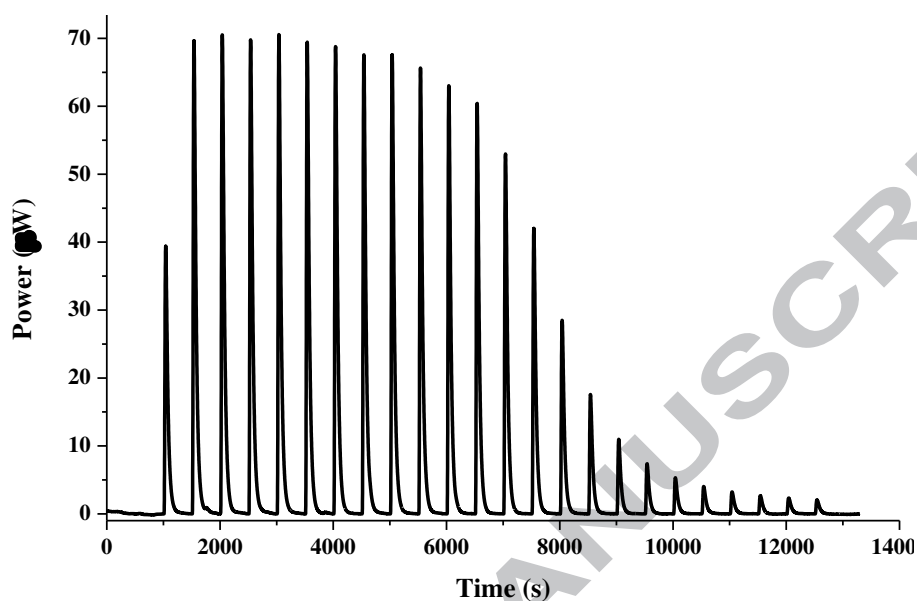


Figure S 7. Isothermal titration calorimetry data for the addition of aliquots of CBPQT^{4+} (10.18mM) to Napht-N-PNIPAM (1.21 mM). Recorded in H_2O at 15°C .

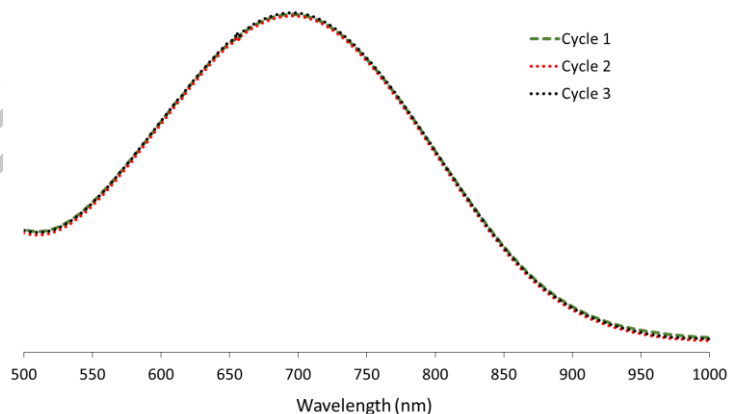


Figure S 8. UV-vis spectra at 20°C of Napht-N-PNIPAM/CBPQT after 3 cycles of heating (over the cloud point) and cooling (cycle 1: green curve, cycle 2: red curve and cycle 3: black curve).

A solution of Napht-N-PNIPAM/CBPQT in water was heated over the cloud point and then cooled down to 20°C . Then, a UV-vis spectrum was recorded demonstrating the presence of the charge transfer band. Three cycles were carried out to prove the reversibility of the complexation/dethreading process.

pH = 1 / pH = 7 switching of an aqueous solution of Napht-N-PNIPAM'CBPQT monitored by UV-vis spectroscopy.

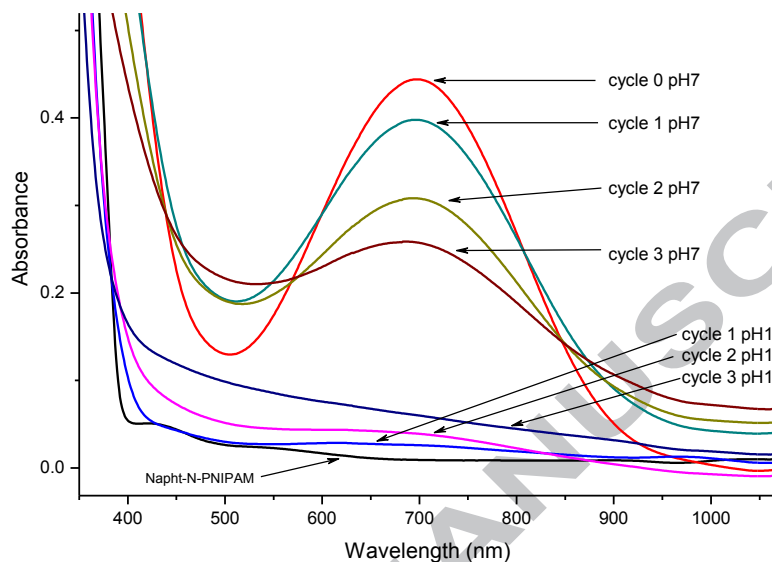


Figure S 9. UV-vis spectra of Napht-N-PNIPAM'CBPQT at pH = 1 and 7

To a solution of Napht-N-PNIPAM'CBPQT in water at pH = 7 (cycle 0, pH7, Figure S 9) were added aliquots of HCl (1M) to obtain pH = 1 (cycle 1, pH1, Figure S 9). It leads to protonation of naphthalene unit located at the end chain of PNIPAM and then to the disruption of the host-guest complex (no absorption band at 697 nm). The process is reversible when aliquots of DABCO (1.5M) are added to the mixture in order to obtain pH = 7 (cycle 1, pH7, Figure S 9) since the band at 697 nm appears. Repeating the procedure of HCl/DABCO additions led to similar results, i.e. disappearance and reappearance of the absorption band (3 cycles in total) without any signs of decomposition (NMR data not shown). The observed decrease of the absorbance upon addition of aliquots is due to the dilution phenomenon in the UV cell.

pH = 1 / pH = 7 switching of an aqueous solution of Napht-N-PNIPAM monitored by ^1H NMR.

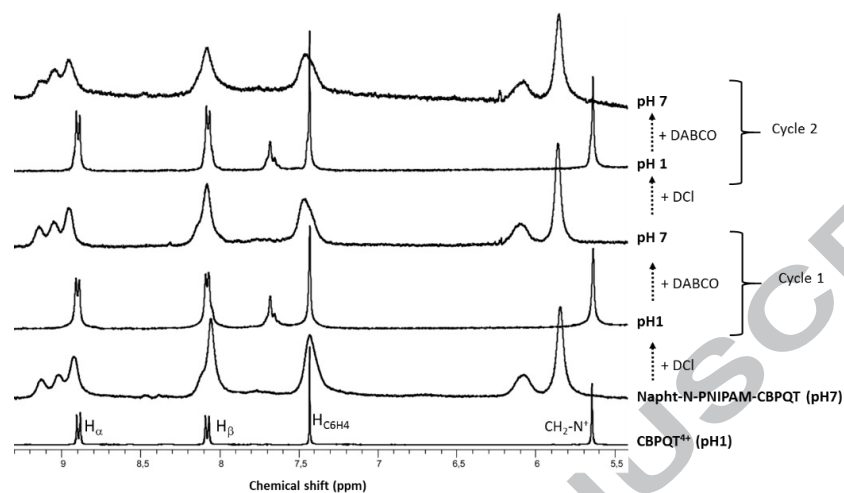


Figure S 10. ^1H NMR spectra of Napht-N-PNIPAM upon the addition of solution of DCl and DABCO (for more clearness, only 2 complete pH = 1/pH = 7 cycles is shown)


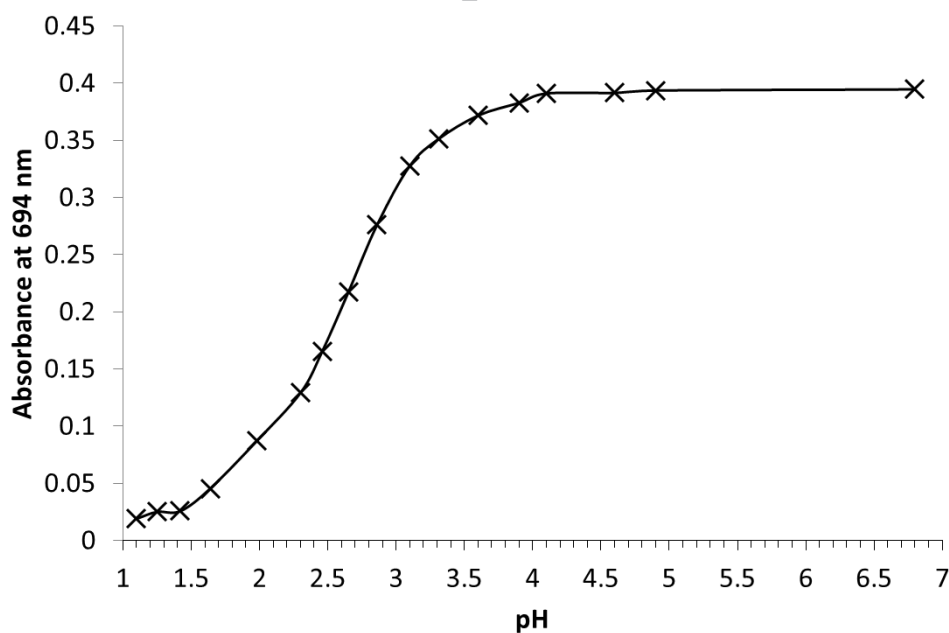


Figure S 11. Titration of Napht-N-PNIPAM.CBPQT (initial pH = 6.8) upon the addition of aliquots of HCl followed by UV-Vis spectroscopy (complex concentration = 13.3 mg/mL H_2O)

References

- [1] Sue C-H, Basu S, Fahrenbach AC, Shveyd AK, Dey SK, Botros YY, et al. Enabling tetracationic cyclophane production by trading templates. *Chem Sci*. 2010;1(1):119-125.
- [2] Qiu X-P, Tanaka F, Winnik FM. Temperature-Induced Phase Transition of Well-Defined Cyclic Poly(N-isopropylacrylamide)s in Aqueous Solution. *Macromolecules*. 2007;40(20):7069-7071.

Graphical Abstract

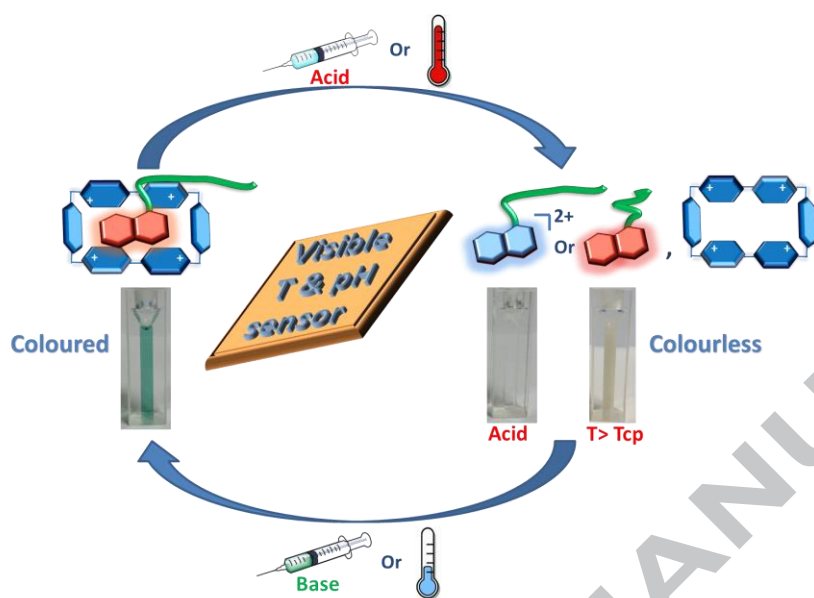

Highlights :

- Synthesis of a multi-stimuli responsive diaminonaphthalene functionalized PNIPAM
- Elaboration of a water-soluble host-guest supramolecular polymeric dual sensor
- The pseudorotaxane polymer architecture can be reversibly dissociated on demand

ACCEPTED MANUSCRIPT