

Complex Permittivity Measurements of Common Plastics Over Variable Temperatures

Bill Riddle, James Baker-Jarvis, *Senior Member, IEEE*, and Jerzy Krupka, *Senior Member, IEEE*

Abstract—In this paper, we present complex permittivity data at microwave frequencies (approximately 10 GHz) for many common plastics over a temperature range of 122 to 375 K. The measurements were made with a $TE_{01\delta}$ dielectric resonator placed inside an environmental chamber. Data are presented for the following materials: acrylonitrile butadiene styrene, polytetrafluoroethylene, cross-linked polystyrene, tetrafluoroethylene-perfluorpropylene, polypropylene, polysulfone, polymethylmethacrylate, polyvinyl chloride, polycarbonate, high-density polyethylene, polyoxy-methylene (acetal homopolymer), and polyamide.

Index Terms—Complex permittivity, dielectric resonator, microwave frequency, plastics, variable temperatures.

I. INTRODUCTION

PLASTICS ARE used in many areas of manufacturing and have naturally found application in the construction of electronic devices. As the operating frequencies of these devices continue to increase, designers need accurate data of the electromagnetic properties of these materials. There is a sizable body of data in the technical literature about the electromagnetic properties of plastics, but most of those results focus on only a few materials. Permittivity measurements at various temperatures and frequencies for some of the materials presented here can be found in [1]–[9]. An excellent review article presenting data on many plastics with extensive references is given in [10]. Data for several plastic materials using different techniques are presented in [11] and [12].

In this paper, we present complex permittivity data of many common plastics at a frequency of approximately 10 GHz and over the temperature range of 122 to 375 K. The plastics measured are as follows: polytetrafluoroethylene (PTFE), cross-linked polystyrene (CPS), tetrafluoroethylene-perfluorpropylene (FEP), polypropylene, polysulfone, polymethylmethacrylate (PMMA), polyvinyl chloride (PVC), polyoxy-methylene (acetal homopolymer), polycarbonate, high-density polyethylene (HDPE), polyamide (nylon), and acrylonitrile butadiene styrene (ABS).¹

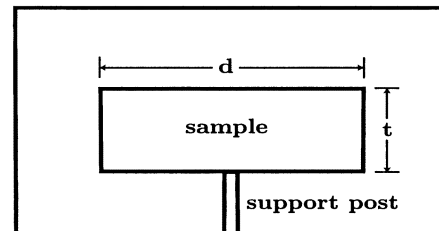


Fig. 1. Cross section of the $TE_{01\delta}$ dielectric resonator.

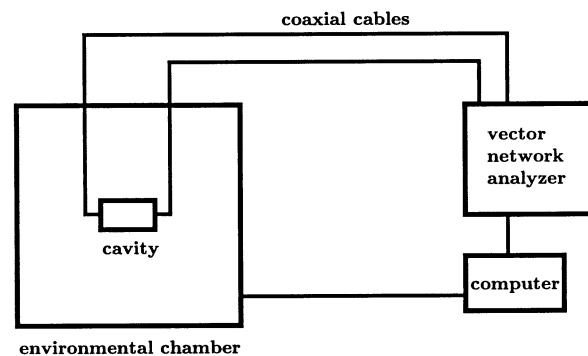


Fig. 2. Schematic diagram of the measurement system.

II. DESCRIPTION OF THE MEASUREMENT SYSTEM

In our previous paper [13], we described the use of a cylindrical $TE_{01\delta}$ dielectric resonator for measuring the complex permittivity of cylindrical samples of dielectric material over a variable temperature range. A cross-sectional diagram of the resonator geometry with a typical dielectric sample supported by a dielectric post is shown in Fig. 1. The cylindrical cavity is constructed out of metal, and the fields within the sample are excited by coupling loops (not shown) that can be varied to control the amount of electromagnetic energy coupled into the sample.

Fig. 2 shows a schematic diagram of the measurement system with the $TE_{01\delta}$ cavity placed inside an environmental chamber and connected to a vector network analyzer (VNA) through coaxial bulkhead connectors. At each temperature, the dielectric sample was allowed to reach thermal equilibrium by maintaining a constant chamber temperature for one hour. The magnitude of the transmission parameter S_{21} was measured with the VNA to obtain the resonant frequency and quality factor Q of the resonator using the 3-dB method [14]. Effort was made to maintain the cavity coupling below -45 dB to minimize systematic effects due to the coupling loops. The procedure was automated by use of a computer to control the system.

Manuscript received November 7, 2001; revised October 15, 2002.

B. Riddle and J. Baker-Jarvis are with the Radio-Frequency Technology Division, National Institute of Standards and Technology (NIST), Boulder, CO 80305-3328 USA (e-mail: Bill.Riddle@nist.gov).

J. Krupka is with the Warsaw University of Technology, Warsaw 00-662, Poland.

Digital Object Identifier 10.1109/TMTT.2003.808730

¹Specific materials that are commonly used are mentioned for informational purposes only. This does not imply or constitute any endorsement by the National Institute of Standards and Technology.

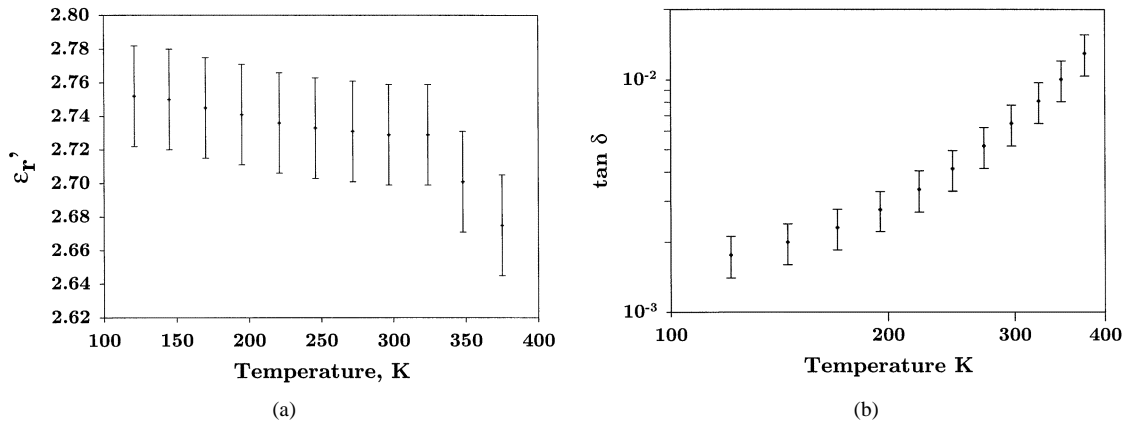


Fig. 3. Acetal homopolymer, $f \approx 11$ GHz. (a) Relative permittivity versus temperature. (b) Loss tangent versus temperature.

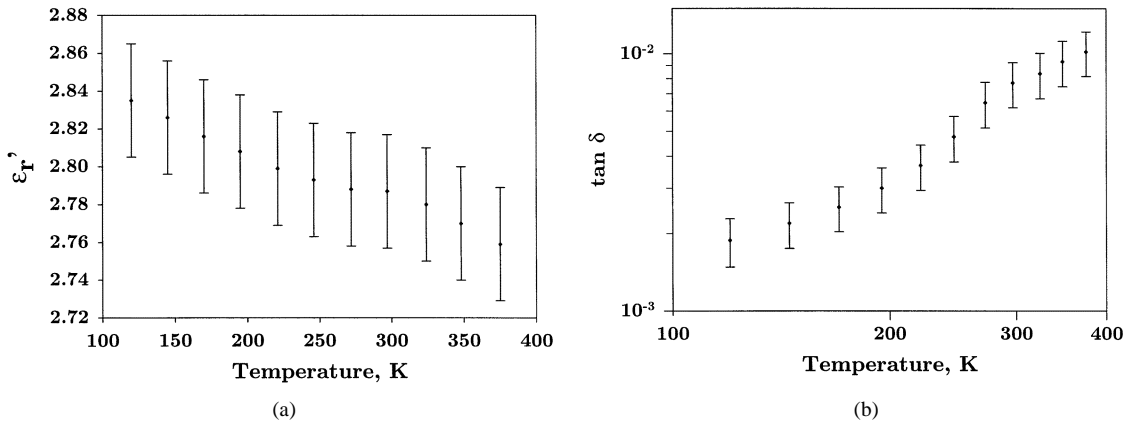


Fig. 4. Acrylonitrile butadiene styrene, $f \approx 11$ GHz. (a) Relative permittivity versus temperature. (b) Loss tangent versus temperature.

For a dielectric material that is homogeneous, linear, and isotropic, the complex permittivity ϵ is defined by

$$\mathbf{D}(\omega) = \epsilon(\omega)\mathbf{E}(\omega) \quad (1)$$

where \mathbf{E} is the complex time-harmonic steady-state electric field, \mathbf{D} is the corresponding electric flux density, and ω is the radian frequency [15]. For complex time-harmonic fields, it is useful to express ϵ in terms of real and imaginary components

$$\epsilon(\omega) = \epsilon_0(\epsilon_r'(\omega) - j\epsilon_r''(\omega)) \quad (2)$$

where ϵ_0 is the permittivity of vacuum. The measurements in this paper are reported in terms of the relative permittivity ϵ_r' and the dielectric loss tangent, defined as

$$\tan \delta(\omega) = \frac{\epsilon_r''(\omega)}{\epsilon_r'(\omega)}. \quad (3)$$

After measuring the resonant frequency and Q at each temperature for the materials under test, we were able to calculate ϵ based on the algorithm described in [13].

III. THERMAL EXPANSION

The algorithm used in calculating ϵ is very sensitive to variations in sample dimensions, which in turn are functions of temperature. Therefore, it is important to take into account the effect of thermal expansion on the samples during a measurement. In

general, for a given material, the coefficient of linear thermal expansion α at constant pressure P is defined by [16]

$$\alpha = \frac{1}{l} \left(\frac{\partial l}{\partial T} \right)_P \quad (4)$$

where T is the temperature and l is the linear dimension of interest. Assuming that l is a function only of T , the resulting separable ordinary differential equation can be solved as

$$l_1 = l_0 \exp \left(\int_{T_0}^{T_1} \alpha dT \right) \quad (5)$$

where l_0 and l_1 are the linear dimensions at temperatures T_0 and T_1 , respectively. Data for the thermal expansion coefficient α are available for many of the materials measured in this work [16], [17]. Using the data for α with the expression for l_1 above, we were able to correct for the expansion of the measured samples due to changing temperature.

IV. MEASUREMENT RESULTS

The results of the temperature-variable measurements of the plastic materials are shown in Figs. 3–15. Each figure caption includes the approximate resonant frequency of the cavity containing the sample at ambient temperature. Of course, this frequency varies as the properties and dimensions of the sample and cavity change with temperature. The samples measured were machined from common industrial-grade sources, with no

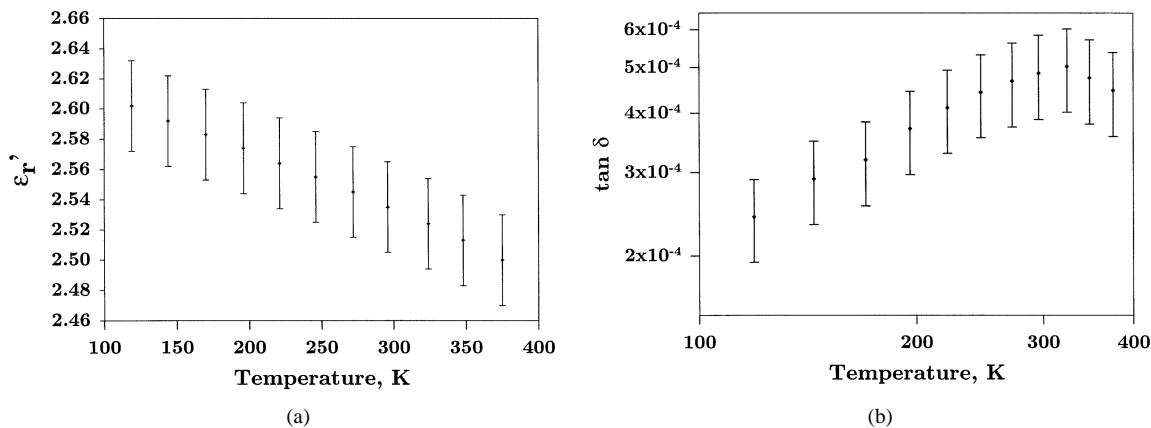


Fig. 5. Cross-linked polystyrene, $f \approx 10.7$ GHz. (a) Relative permittivity versus temperature. (b) Loss tangent versus temperature.

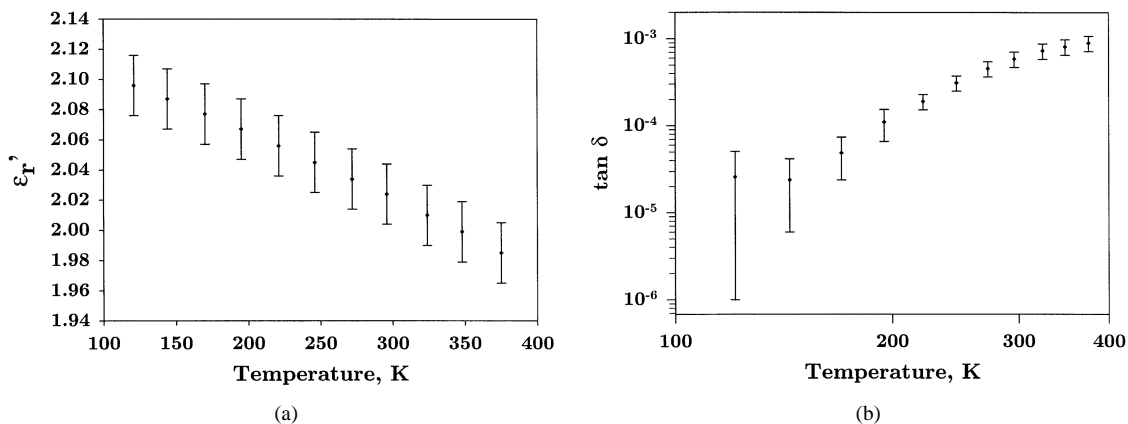


Fig. 6. Tetrafluoroethylene-perfluoropropylene, $f \approx 10.4$ GHz. (a) Relative permittivity versus temperature. (b) Loss tangent versus temperature.

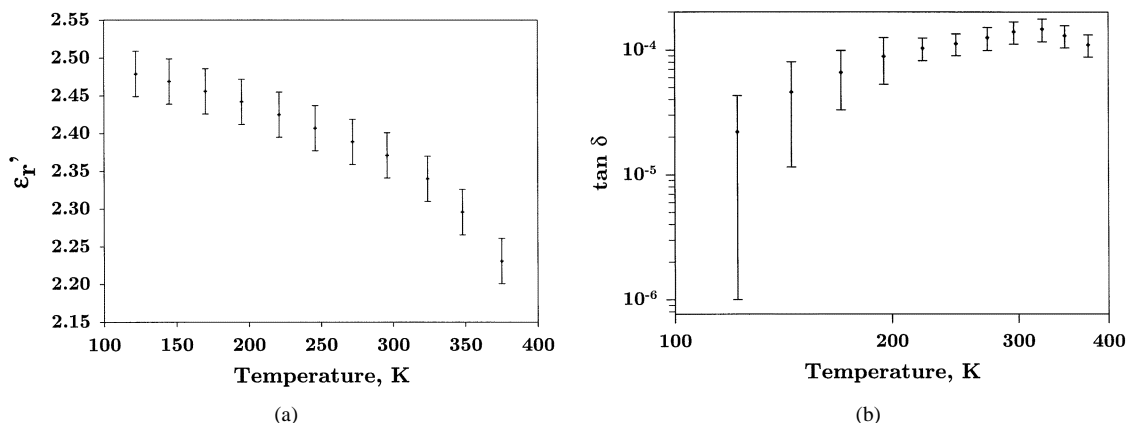


Fig. 7. High-density polyethylene, $f \approx 11.3$ GHz. (a) Relative permittivity versus temperature. (b) Loss tangent versus temperature.

precise information about their exact chemical composition. A common characteristic of plastics is that the composition, and therefore the electrical properties, can vary considerably between different manufacturers and sometimes within different production lots of the same manufacturer. We have not made any effort to analyze or control this possible systematic effect on the data presented here.

V. UNCERTAINTY ANALYSIS

A detailed explanation of the procedure we used to evaluate the standard uncertainty of our measurements can be found in

[18]. The standard uncertainty of a measurement is denoted by $u(x_i)$, where x_i is the best estimate of the input quantity of the measurand of interest. All input quantities are assumed to be independent, although in general this assumption is very weak. The combined standard uncertainty of a measurand θ is defined as

$$u_c(\theta) = \sqrt{\sum_i \left(u(x_i) \frac{\partial \theta}{\partial x_i} \right)^2}. \quad (6)$$

The two measurands in this paper are ϵ_r' and $\tan \delta$. In general, uncertainties that can be evaluated by statistical methods are

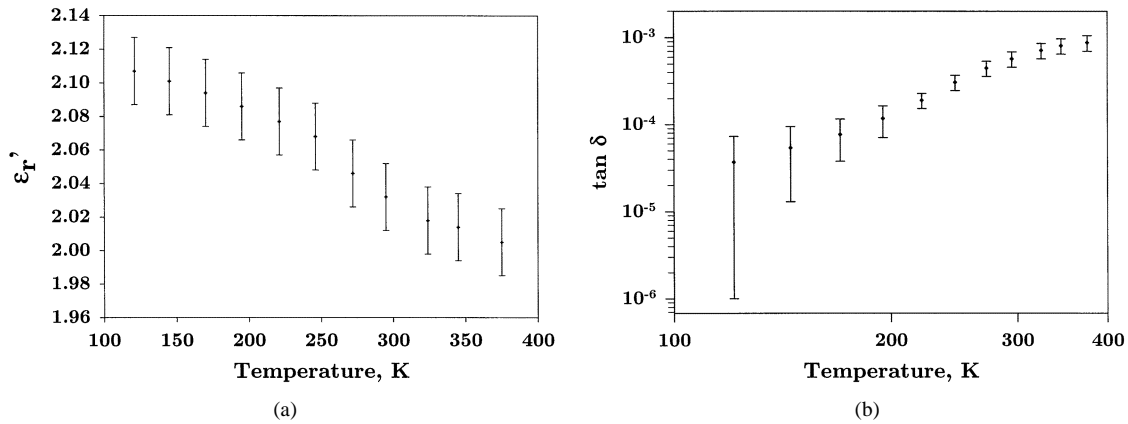


Fig. 8. High-density polytetrafluoroethylene, $f \approx 11.5$ GHz. (a) Relative permittivity versus temperature. (b) Loss tangent versus temperature.

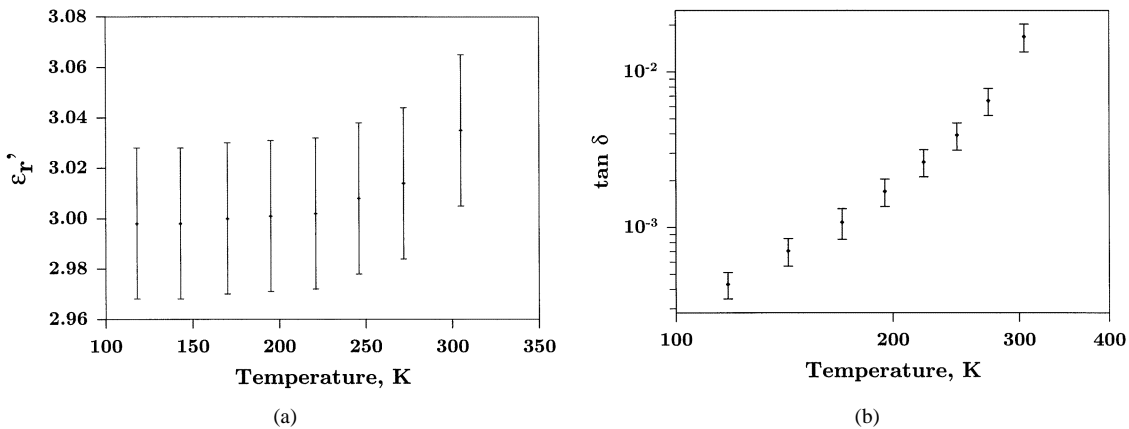


Fig. 9. Polyamide, $f \approx 10.8$ GHz. (a) Relative permittivity versus temperature. (b) Loss tangent versus temperature.

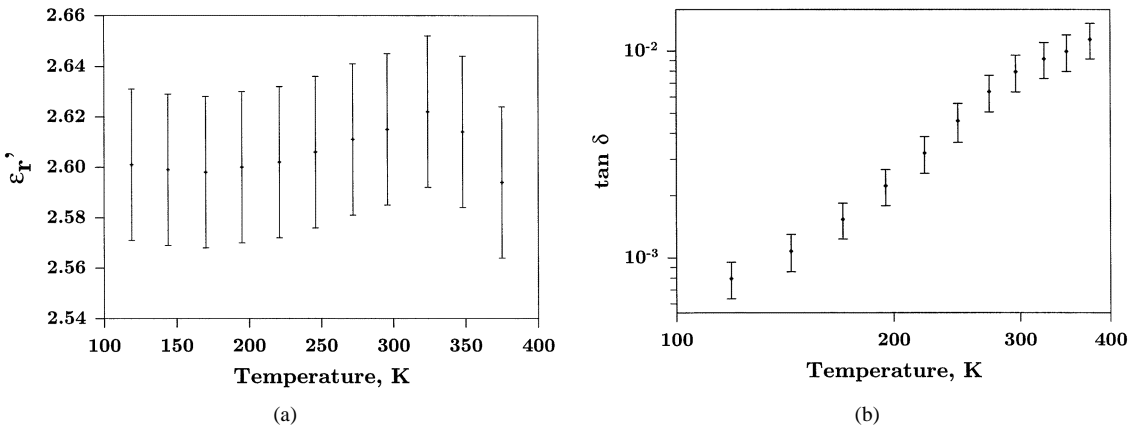


Fig. 10. Polymethylmethacrylate, $f \approx 11$ GHz. (a) Relative permittivity versus temperature. (b) Loss tangent versus temperature.

termed Type A (reported with degrees of freedom ν), and all others as Type B. The reported uncertainties of the results shown in Figs. 3–15 are given in terms of the expanded uncertainty of a measurand θ , defined as [18]

$$U(\theta) = k u_c(\theta) \quad (7)$$

where k is the coverage factor. We have used a value of $k = 2$ for $U(\epsilon_r')$ and $U(\tan \delta)$.

Performing the uncertainty calculations on every sample at every temperature proved to be impractical, so instead extensive calculations of the measurement uncertainties were performed

on two representative materials (PTFE and CPS). Although we have attempted to include the dominant sources of measurement uncertainty in these calculations, some sources (e.g., temperature effects on the coaxial cables) could not be included.

The input quantities that significantly contribute to the combined standard uncertainty of ϵ_r' are the sample thickness t , the sample diameter d (see Fig. 1), and the cavity calibration found by use of a reference material, denoted q . This functional relationship can be expressed as

$$\epsilon_r' = f(t, d, q). \quad (8)$$

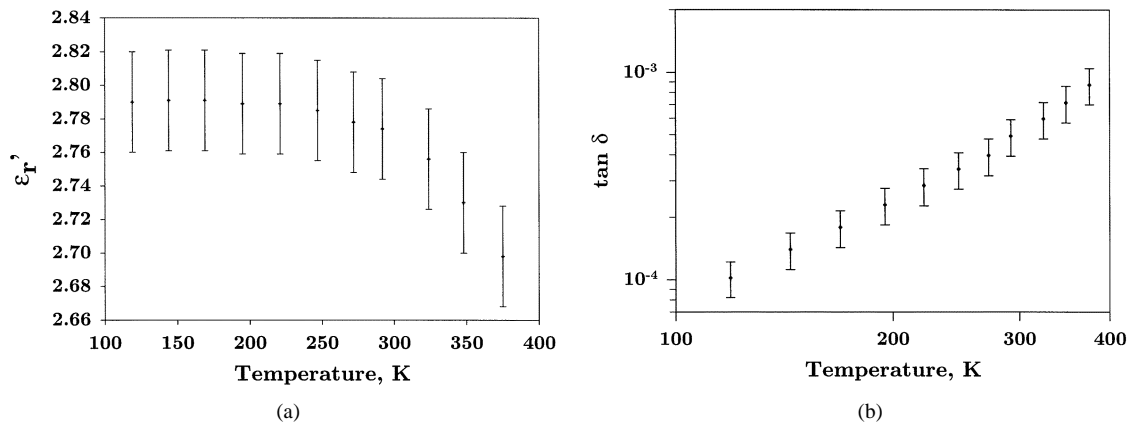


Fig. 11. Polycarbonate, $f \approx 11$ GHz. (a) Relative permittivity versus temperature. (b) Loss tangent versus temperature.

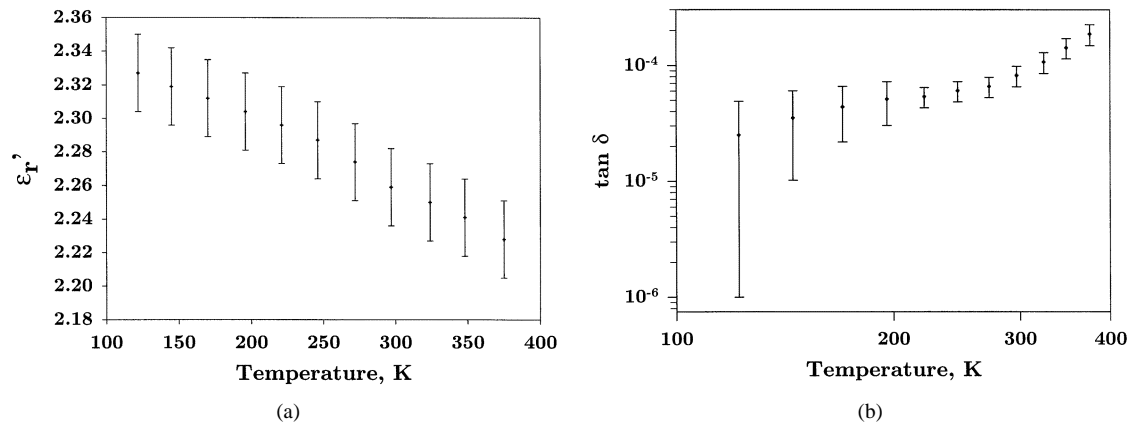


Fig. 12. Polypropylene, $f \approx 9.4$ GHz. (a) Relative permittivity versus temperature. (b) Loss tangent versus temperature.

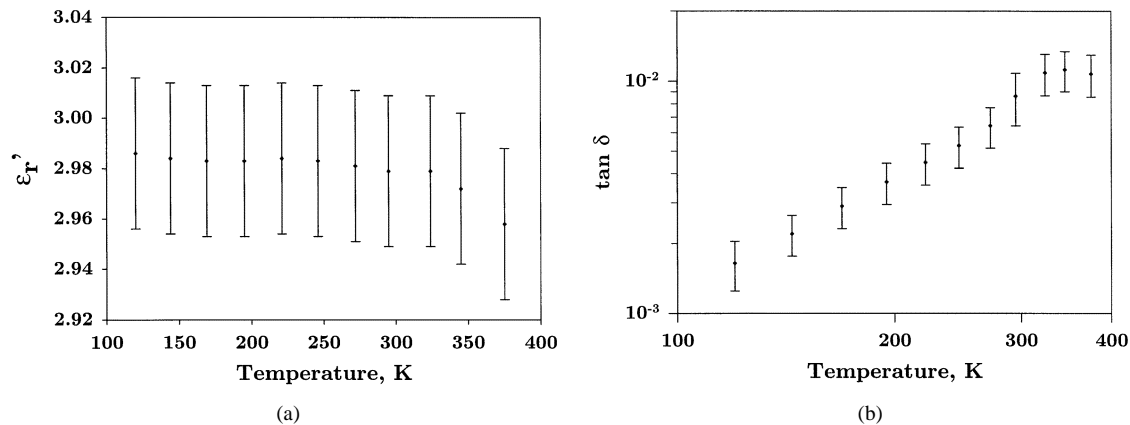


Fig. 13. Polysulfone, $f \approx 10.8$ GHz. (a) Relative permittivity versus temperature. (b) Loss tangent versus temperature.

The function f is defined through the numerical algorithms described in [13]. The dimensional uncertainties $u(t)$ and $u(d)$ were obtained from repeated measurements of the sample at ambient temperature and pressure (297 K and 84 kPa). A well-characterized reference material (quartz) was used to calibrate the systematic effect due to the cavity post height, and $u(q)$ was obtained from the uncertainty in the value of ϵ of the reference material.

Listed in Table I are the values used in calculating the combined standard uncertainty for ϵ_r' . The partial derivatives were obtained by numerically varying the input quantity of interest by a small amount and noting the effect in ϵ_r' . By use of the

values in Table I, the combined relative uncertainty of ϵ_r' was found to be

$$\frac{u_c(\epsilon_r')}{\epsilon_r'} = \pm 0.5\%. \quad (9)$$

The uncertainty in the measurement of $\tan \delta$ was dominated by the Type B measurement uncertainties of Q and R_s , the surface resistance of the metal cavity walls. For measurements performed at ambient temperature, the contributions for each of these factors is shown in Table II [13]. In order to determine the effect of $u(Q)$ and $u(R_s)$ on $u_c(\tan \delta)$, we performed a sensitivity analysis on measurement data instead of using

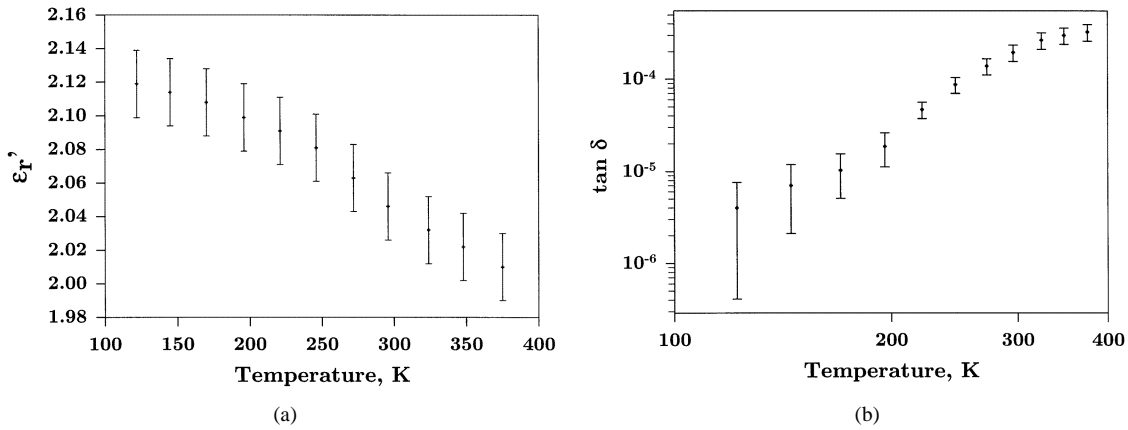


Fig. 14. Polytetrafluoroethylene, $f \approx 10$ GHz. (a) Relative permittivity versus temperature. (b) Loss tangent versus temperature.

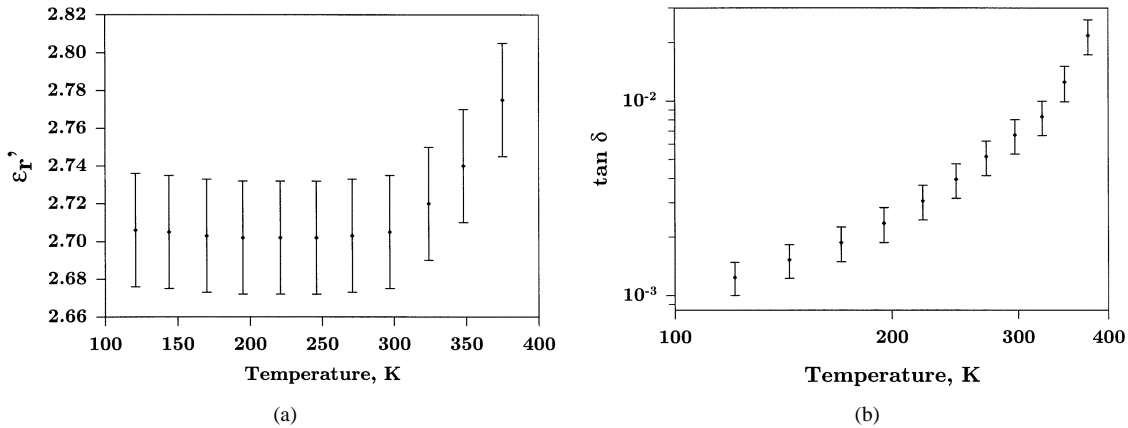


Fig. 15. Polyvinylchloride, $f \approx 11$ GHz. (a) Relative permittivity versus temperature. (b) Loss tangent versus temperature.

TABLE I
RELATIVE UNCERTAINTY COMPONENTS FOR ϵ_r'

Component	Method of Evaluation	Value %
$u(t)(\partial\epsilon_r'/\partial t)$	Type A, $\nu = 29$	0.1
$u(d)(\partial\epsilon_r'/\partial d)$	Type A, $\nu = 29$	0.1
$u(q)(\partial\epsilon_r'/\partial q)$	Type B	0.5

direct calculations based on (6). This was necessary because of the way the numerical model accessed values for R_s . For most of the materials, the results of these calculations at all temperatures was found to be

$$\frac{u_c(\tan \delta)}{\tan \delta} = \pm 10\%. \quad (10)$$

However, for materials that exhibited very low loss (PTFE, FEP, HDPE, and polypropylene), the contribution from $u(R_s)$ played a much larger role in $u_c(\tan \delta)$, resulting in a nonlinear uncertainty versus temperature, as shown in Table III. Other factors also influenced the measurement of $\tan \delta$, but only for a few of the samples and only at certain temperatures. These systematic effects were the result of Q resonance asymmetry due to mode distortion and excessive cavity coupling (greater than -45 dB) at lower temperatures. Where appropriate, these sources of uncertainty are included in the data presented in

TABLE II
RELATIVE UNCERTAINTY COMPONENTS FOR $\tan \delta$

Component	Method of Evaluation	Value %
$u(Q)(\partial \tan \delta / \partial Q)$	Type B	2
$u(R_s)(\partial \tan \delta / \partial R_s)$	Type B	10

TABLE III
RELATIVE COMBINED UNCERTAINTY FOR $\tan \delta$ OF LOW-LOSS MATERIALS

Temperature, K	Value %
122	± 65
145	± 35
170	± 25
196	± 20
221	± 10
246	± 10
272	± 10
296	± 10
324	± 10
348	± 10
375	± 10

Figs. 3–15 and are estimated based on numerical experiments of the PTFE sample data.

Although the analysis presented here should not be considered exhaustive, it does attempt to reasonably estimate the main sources of measurement uncertainty of the measurands.

VI. CAVEAT

The measurements described in this paper were designed without regard to the temperature limitations of the materials used. Before using any of these materials in any application, the manufacturers data sheets should be consulted to determine the recommended limits of their use.

VII. CONCLUSION

We have presented temperature-dependent data of the complex permittivity of many common plastics at microwave frequencies. The results were presented with an uncertainty analysis based on measurements and experiments of selected representative materials.

ACKNOWLEDGMENT

The authors would like to acknowledge helpful discussions with J. Splett and K. Coakley, both of the National Institute of Standards and Technology (NIST) Information and Technology Laboratory, Boulder, CO, and M. Janezic, Radio-Frequency Technology Division, NIST.

REFERENCES

- [1] P. Ehrlich, "Dielectric properties of teflon from room temperature to 314°C and from frequencies of 10^2 to 10^5 c/s," *J. Res. Nat. Bur. Stand.*, vol. 51, 1953.
- [2] R. K. Kirby, "Thermal expansion of polytetrafluoroethylene from -190° to $+300^\circ$ C," *J. Res. Natl. Bur. Stand.*, vol. 57, pp. 91–94, 1956.
- [3] T. K. Chaki and D. K. Khastgir, "Effect of frequency and temperature on dielectric properties of polypropylene at X-band microwave region," *J. Elastomers Plastics*, vol. 22, pp. 58–70, 1990.
- [4] R. Bergman, F. Alvarez, A. Alegria, and J. Colmenero, "Dielectric relaxation in PMMA revisited," *J. Non-Cryst. Solids*, pp. 580–583, 1998.
- [5] L. Aras and B. M. Baysal, "Dielectric relaxation studies of some linear crosslinked and branched polymers," *J. Polym. Sci. B, Polymer Phys.*, vol. 22, pp. 1453–1460, 1984.
- [6] P. K. C. Pillai and Rashmi, "Dielectric properties of polystyrene and some related polymers," *Int. J. Polymeric Mater.*, vol. 8, pp. 255–263, 1980.
- [7] R. D. McCammon, R. G. Saba, and R. N. Work, "Dielectric properties of polystyrene and some polychlorostyrenes from 4 K to room temperature," *J. Polymer Sci. A, Polym. Chem.*, vol. 7, pp. 1721–1733, 1969.
- [8] K. Mazur, "More data about dielectric and electret properties of poly(methyl methacrylate)," *J. Phys. D, Appl. Phys.*, vol. 30, pp. 1383–1398, 1997.
- [9] Y. Kobayashi and H. Tamura, "Round Robin test on a dielectric resonator method for measuring complex permittivity at microwave frequency," *IEICE Trans. Electron.*, vol. E77-C, pp. 882–887, June 1994.
- [10] A. J. Bur, "Dielectric properties of polymers at microwave frequencies: A review," *Polymer*, vol. 26, pp. 963–977, July 1985.
- [11] J. Baker-Jarvis, R. G. Geyer, J. H. Grosvenor, M. D. Janezic, C. A. Jones, B. Riddle, C. M. Weil, and J. Krupka, "Dielectric characterization of low-loss materials: A comparison of techniques," *IEEE Trans. Dielect. Elect. Insulation*, vol. 5, pp. 571–577, Aug. 1998.
- [12] J. Baker-Jarvis, M. Janezic, B. Riddle, C. L. Holloway, N. G. Paulter, and J. E. Blendell, "Dielectric and conductor-loss characterization and measurements on electronic packing materials," NIST, Boulder, CO, Tech. Note 1520, 2001.
- [13] J. Krupka, K. Derzakowski, B. Riddle, and J. Baker-Jarvis, "A dielectric resonator for measurements of complex permittivity of low loss dielectric materials as a function of temperature," *Meas. Sci. Technol.*, vol. 9, pp. 1751–1756, 1998.
- [14] P. J. Petersan and S. M. Anlage, "Measurement of resonant frequency and quality factor of microwave resonators: Comparison of methods," *J. Appl. Phys.*, vol. 84, no. 6, pp. 3392–3402, 1998.
- [15] S. Ramo, J. R. Whinnery, and T. V. Duzer, *Fields and Waves in Communication Electronics*, 3rd ed. New York: Wiley, 1994.
- [16] G. Hartwig, *Polymer Properties at Room and Cryogenic Temperatures*. Boston, MA: Kluwer, 1994.
- [17] Y. S. Touloukian, R. K. Kirby, R. E. Taylor, and T. Y. R. Lee, *Thermal Expansion Nonmetallic Solids Thermophysical Properties of Matter*. New York: IFI/Plenum, 1977, vol. 13.
- [18] *Guide to the Expression of Uncertainty in Measurement*, 1 ed., Int. Org. Standard., Geneva, Switzerland, 1993.

Bill Riddle received the B.S. degree in electrical engineering and M.Sc. degree in applied mathematics from the University of Colorado at Boulder.

He is an Electronics Engineer with the Radio-Frequency Technology Division, National Institute of Standards and Technology, Boulder, CO, where he has worked since 1985.

James Baker-Jarvis (M'89–SM'90) was born in Minneapolis, MN, in 1950. He received the B.S. degree in mathematics in 1975, the M.S. degree in physics from the University of Minnesota, Minneapolis, in 1980, and the Ph.D. degree in theoretical physics from the University of Wyoming, Laramie, in 1984.

Following graduation for one year, he was an AWU Post-Doctoral Fellow involved with theoretical and experimental aspects of intense electromagnetic fields in lossy materials and dielectric measurements. He then spent two years as an Assistant Professor with the Physics Department, University of Wyoming, where he was involved with electromagnetic heating processes and taught classes. Through 1988, he was an Assistant Professor of Physics with North Dakota State University (NDSU), where he taught courses in the areas of electronic properties of materials and performed research on an innovative technique to solve differential equations using a maximum-entropy technique. In January, 1989, he joined the National Institute of Standards and Technology (NIST), Boulder, CO, where he has been involved in the areas of theory of microscopic relaxation, electronic materials, dielectric and magnetic spectroscopy, and nondestructive evaluation. He is Project Leader of the Electromagnetic Properties of Materials Project with NIST. He has authored numerous publications. His current interests are dielectric measurement metrology and theoretical microscopic electromagnetism.

Dr. Baker-Jarvis is a NIST Bronze Medal recipient.

Jerzy Krupka (M'00–SM'01) was born in Cracow, Poland, in 1949. He received the M.Sc. (with honors), Ph.D., and habilitation degrees from the Warsaw University of Technology, Warsaw, Poland, in 1973, 1977, and 1989, respectively.

Since 1973, he has been with the Institute of Microelectronics and Optoelectronics, Warsaw University of Technology, where he is currently a Professor. His research deals mainly with measurements of the electric and magnetic properties of materials at microwave frequencies and he is an international expert in this field. He was a leader and took part in several research projects on these subjects in the U.S., U.K., Australia, Germany, and France. He has authored or coauthored over 100 papers appearing in international journals, encyclopedias, and conference proceedings.

Dr. Krupka has been an Editorial Board member for the IEEE TRANSACTIONS ON MICROWAVE THEORY AND TECHNIQUES since 1994. He was the recipient of the 1999 Best Paper Award in Measurements Science and Technology (U.K.).