

## Toward a reference material for line profile analysis

Andrea Troian,<sup>1</sup> Luca Rebuffi,<sup>1,2</sup> Matteo Leoni,<sup>1</sup> and Paolo Scardi<sup>1,a)</sup>

<sup>1</sup>Department of Civil, Environmental and Mechanical Engineering, University of Trento, Trento, Italy

<sup>2</sup>Elettra-Sincrotrone Trieste S.C.p.A., Trieste, Italy

(Received 15 September 2014; accepted 17 November 2014)

A powder obtained by ball milling a commercial FeMo alloy has been identified and investigated as possible reference material for powder diffraction line profile analysis. Ball milling yields micrometer-scale agglomerate particles made of rounded nanocrystalline domains with extensive lattice defects, so as to produce both size and strain contributions to the line profiles. The capability of a modern whole-powder pattern modeling to accurately quantify those aspects and the stability of the powder over a decade are shown and discussed. © 2014 International Centre for Diffraction Data. [doi:10.1017/S0885715614001298]

Key words: line profile analysis, whole-powder pattern modeling, ball milling, FeMo

### I. INTRODUCTION

Line profile analysis (LPA) is a typical application of diffraction providing microstructure information from a wide class of crystalline materials, ranging for example, from organic/pharmaceutical to ceramics and metals. Simple methods, some of them are known for almost a century, are described in traditional textbooks (Klug and Alexander, 1974; Schwartz and Cohen, 1977; Guinebretiere, 2007; Dinnebier and Billinge, 2008), and are routinely used by several laboratories of an order of magnitude estimate for example, of the domain size in nanocrystalline powders. The research is still strong in the field and important milestones have been reached in the past 20 years (Snyder *et al.*, 2000; Mittemeijer and Scardi, 2004); full pattern methods have been developed considerably, to provide information that can nowadays easily complement electron microscopy observations.

It is often considered that LPA does not require highly sophisticated or advanced instruments for data collection, as the interest is in broadened line profiles. This is partly true, as it is relatively easy and straightforward to collect powder diffraction data and assess the peak profile width, but a proper evaluation of the data is still important, especially when accurate quantitative information is sought. For example, the instrumental profile function (IPF, the instrumental contribution to the observed diffraction line profile) should be carefully determined, especially when the width of the observed line profiles approaches the instrumental resolution. More significantly with synchrotron radiation (SR), beamlines can collect high-energy X-ray diffraction (XRD) data so as to encompass a large number of peaks and significantly increase the resolution and information content in a powder pattern; better statistics can also be relevant to appreciate fine details in the peak shape, and properly solve line profile overlapping.

With so many issues and given the variety of available LPA methods with the absence of a microstructure standard, the availability of a fully characterized reference material can be useful to test instrument features and performance, data collection, and reduction procedures.

Among the many possible reference candidates, a ball milled iron-alloy powder seems the ideal one for the possibility of assessing both domain size and strain contributions to the line profiles in the same powder pattern. The simple body centered cubic (bcc) crystal structure gives in fact relatively few peaks: this is of key importance to minimize peak overlapping and to provide, at the same time, intense, and easily measurable diffraction signals.

In the search for appropriate materials and operating conditions to produce a sufficiently large batch of ball milled powder, stability in time is a primary need and a basic starting point to develop a reference material. In the present work, the stability of the suggested material is demonstrated over a time range of 10 years, also providing a preliminary assessment of size/strain values that can be measured in a ball milled iron alloy. Standardization and scaling up to produce suitably large amounts of powder are then a relatively simple step forward.

### II. EXPERIMENTAL

The metal powder of this study is a commercial Fe–1.5 wt% Mo alloy (Astaloy Mo<sup>®</sup>), easily available in large quantities and at a low cost, requiring no special care for handling and storage. Grinding was made in a planetary ball mill (Fritsch Pulverisette P4), using steel jars and 100Cr6 steel balls for 128 h. All operating parameters were suitably optimized in a previous study (D'Incau *et al.*, 2007), aiming at producing a uniform material with limited contamination from the grinding media. A lubricant (96% vol. ethanol) was added to prevent cold welding or sticking of the powder to the jar walls. To avoid oxidation, grinding was performed in a controlled Ar atmosphere (2% vol. O<sub>2max</sub>).

Powder diffraction laboratory data were collected on a Rigaku PMG-VH instrument, based on the traditional

<sup>a)</sup>Author to whom correspondence should be addressed. Electronic mail: Paolo.Scardi@unitn.it

Bragg–Brentano configuration with a vertical flat-plate sample holder. A graphite bent crystal-analyzer in the diffracted beam was used to filter the Cu radiation produced by a sealed X-ray tube. Together with narrow slits ( $1^\circ$  divergence slit,  $2^\circ$  soller slits, and 0.15 mm receiving slit), the optical setup of the diffractometer was such to produce narrow and symmetrical instrumental line profiles across the whole range of required diffraction angles. The IPF was evaluated experimentally with a  $\text{LaB}_6$  standard (Staudemann *et al.*, 2000), using pseudoVoigt (pV) functions to fit the instrumental line profiles. The trend of the full-width half-maximums (FWHM) was parameterized refining the coefficients of the well-known Caglioti's expression (Caglioti *et al.*, 1958), whereas a simple polynomial was used to fit the trend of the Lorentzian fraction (mixing) parameter.

SR XRD data were collected at ESRF (Grenoble, F), ID31 beamline (now moved to ID22), using the standard capillary sample holder of the Debye–Scherrer geometry with a 20 keV (0.063 25 nm) monochromatic beam. The IPF was determined using the same procedure described above for the laboratory XRD data.

### III. RESULTS AND DISCUSSION

As shown by the SEM micrographs [see Figures 1(a) and 1(b)], mechanical grinding yields a powder of agglomerate particles, which even after an extensive milling ranges from a few to a few tens of micrometers in size. When observed

at high magnification, as shown in Figure 1(c), agglomerates show finer features, about 10–20 nm and smaller, which are likely in the size range of the crystalline domains contributing to the diffraction line profiles. Such an agglomeration is a positive feature for the purpose of producing a stable iron-alloy powder, as the inevitable passivation only affects the surface of the agglomerates, thus drastically limiting the oxidation of the metallic nanocrystalline domains.

Stability of the ball milled FeMo alloy powder is demonstrated by the XRD results. XRD data are shown plotting the intensity versus the reciprocal distance  $1/d$ , defined as  $1/d = 2/\lambda[\sin(\theta)]$ . This allows a direct comparison of instrumental resolution for the XRD data collected with different wavelengths. Figure 2 shows a comparison of powder patterns collected as the sample of this study by the same instrument at a distance of 10 years. The two patterns look remarkably similar, even considering that differences in the instrument are also to be expected after 10 years of use, maintenance, and substitution of the X-ray source.

Further evidence on the stability of the ball milled powder is provided by LPA, using the whole-powder pattern modeling (WPPM) approach (Scardi and Leoni, 2002, 2006, Scardi *et al.*, 2010). The XRD powder data were modeled assuming spherical crystalline domains with a lognormal distribution of diameters, using lognormal mean and variance as refinable parameters. Microstrain effects were completely attributed to dislocations, described within the framework of the Krivoglaž–Wilkins (KW) theory (Krivoglaž and

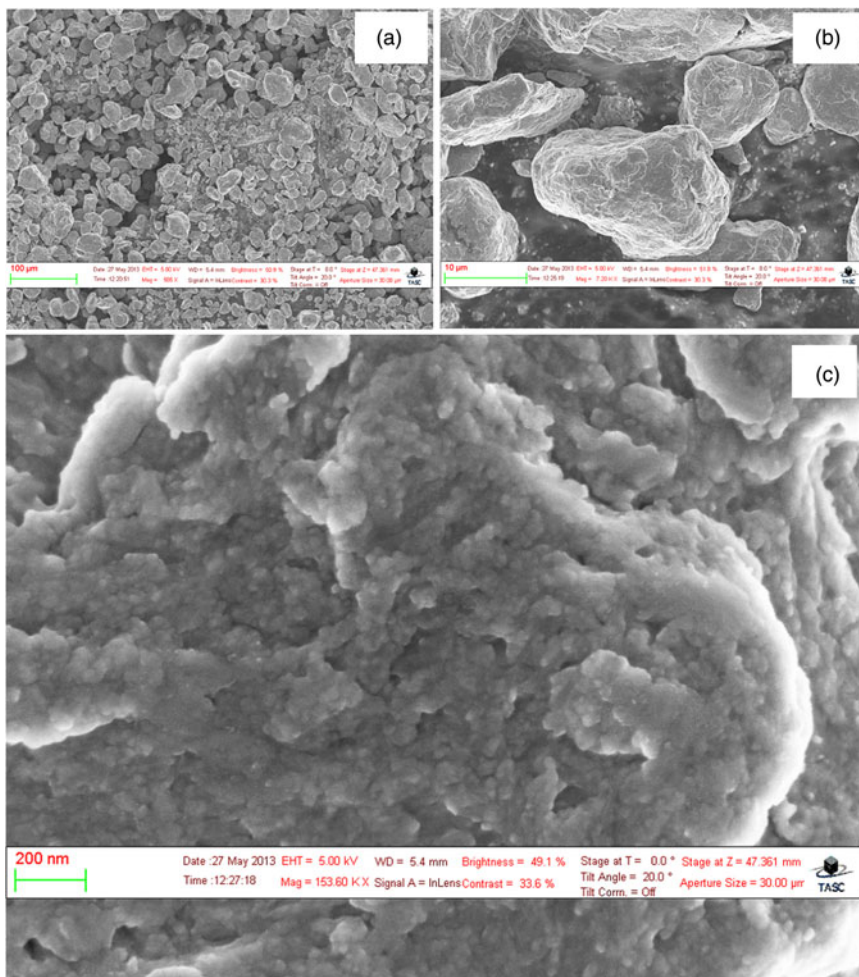


Figure 1. (Color online) SEM micrographs of the FeMo alloy powder ball milled for 128 h (courtesy of R. Ciancio, CNR-Tasc, Trieste). Agglomerate particles are shown in Figures 1(a) and 1(b), whereas a high magnification picture 1(c) highlights the nanoscale features visible on the agglomerate surface. See text for details.

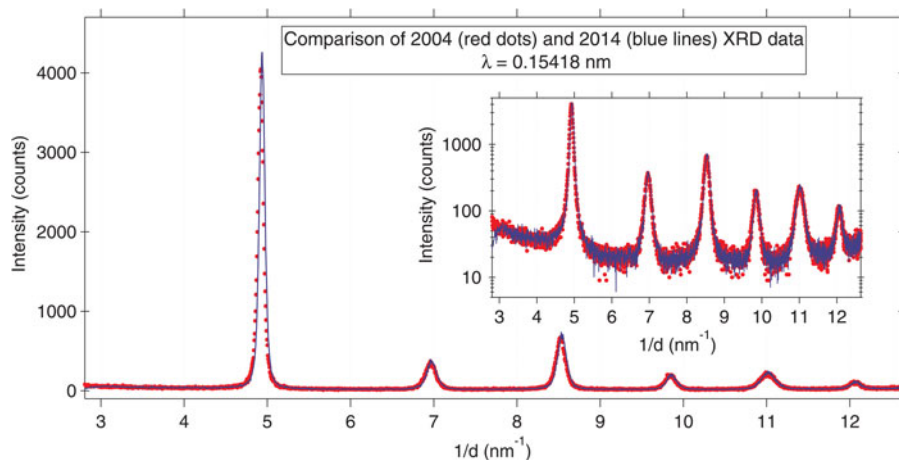


Figure 2. (Color online) Comparison of XRD patterns of the powder of this study, a FeMo alloy ball milled for 128 h, collected by the same instrument at a distance of 10 years (respectively 2004 and present day 2014).

Ryaboshapka, 1963; Wilkens, 1970a, 1970b; Martinez-Garcia *et al.*, 2009) in terms of edge/screw dislocations in the primary slip system of iron; refined parameters were: the average dislocation density ( $\rho$ ), effective outer cut-off radius ( $R_c$ ), and fraction of edge/screw dislocation types ( $f_E$ ). The unit-cell parameter ( $a_0$ ) was also refined, whereas the IPF was previously determined on a standard  $\text{LaB}_6$  powder pattern and then convolved with the line profiles of the size and strain contributions. Details of the procedure are available in the literature on the WPPM method (Scardi and Leoni, 2002, 2006; Leoni *et al.*, 2006; Scardi *et al.*, 2010). Further parameters of WPPM include aberrations in sample position and coefficients of a Chebyshev polynomial background.

WPPM results are shown in the graphical form in Figure 3, whereas Table I reports the statistical indices and the most significant microstructural refinement parameters

used in the fitting procedure. Figure 3 also shows the details of instrumental component (FWHM and Lorentzian fraction as a function of  $1/d$ ). It is quite evident the higher resolution (i.e., smaller FWHM) of the SR XRD data, which also includes a larger number of peaks than the traditional laboratory XRD data [cf. Figures 3(a)–3(c)].

The stability of the ball milled powder is quite evident by comparing WPPM results for data collected on 2004 and 2014, and the corresponding result is of a joint refinement of the two datasets (same microstructural parameters for both datasets; specimen displacement from the diffractometer axis, IPF, and background are specific to each dataset). Differences, if present, are within the estimated standard deviations, with the exception of the unit-cell parameter, which tends to be affected by the broadness of the peak profiles, and likely correlates with the instrumental errors (specimen

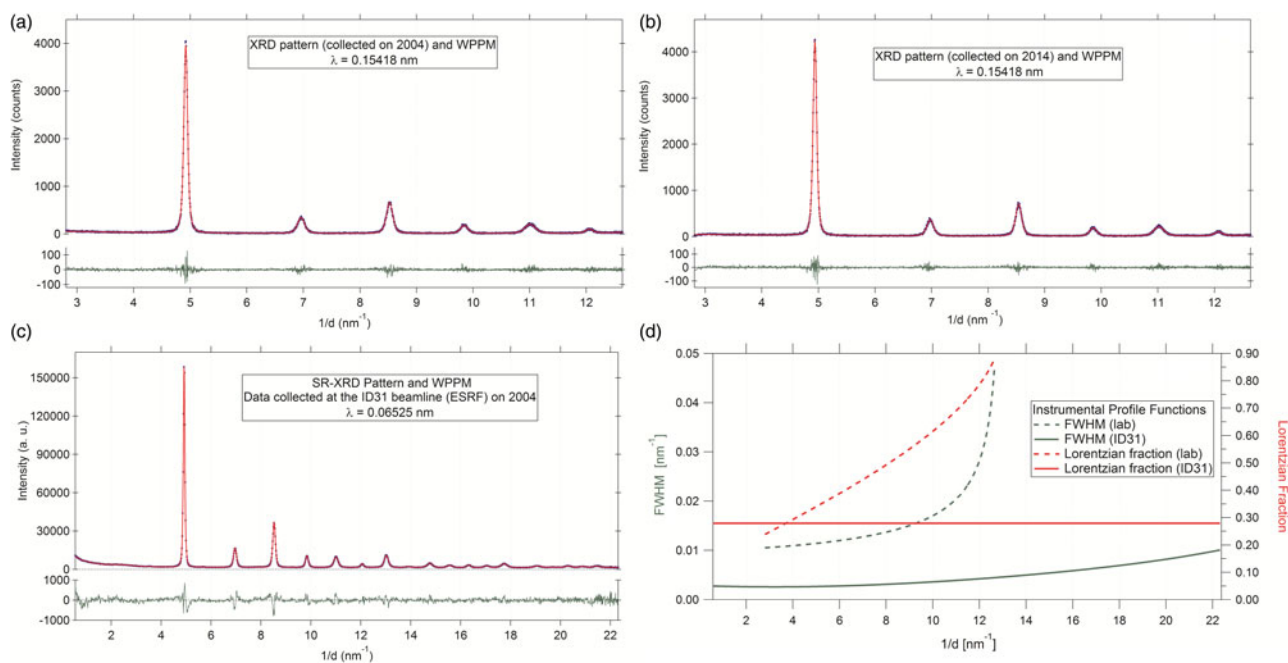


Figure 3. (Color online) Graphical result of WPPM for the powder data of Figure 2, referred to measurements collected on 2004 (a) and 2014 (b). It is also shown the WPPM of an SR-XRD pattern collected on 2004 (c). IPF data (d): FWHM and Lorentzian profile fraction for the laboratory XRD data in (a) and (b) (dash), and SR XRD in (c) (line).

TABLE I. WPPM results and statistics for data collected on 2004, 2014, combined fit of both datasets (2004 & 2014), and SR XRD data (2004 SR): unit-cell parameter ( $a_0$ ), average dislocation density ( $\rho$ ), effective outer cut-off radius ( $R_c$ ), fraction of edge/screw dislocations ( $f_E$ ), Wilkens parameter  $\text{Re} \cdot \sqrt{\rho}$ , mean domain size (diameter,  $\langle D \rangle$ ) and standard deviation (s.d.), specimen displacement; Weighted sum of squares (WSS), Goodness of Fit (GoF); number of refined parameters (Nfit); and total number of data points (Nobs). Estimated standard deviation (e.s.d.) are given in parentheses, referred to the last significant digit.

	2004	2014	2004 & 2014	2004 SR
$a_0$ (nm)	0.287 32(2)	0.287 10(2)	0.287 21(1)	0.287 294(6)
$\rho$ ( $\text{m}^{-2}$ )	0.024(1)	0.021(1)	0.0224(6)	0.0216(3)
$R_c$ (nm)	12(1)	13(1)	12.5(8)	11.9(3)
$f_E$	0.61(3)	0.63(3)	0.62(2)	0.61(1)
$R_c \sqrt{\rho}$	1.9(10)	1.9(10)	1.9(9)	1.7(5)
$\langle D \rangle$ (nm)	18.2(15)	17.8(15)	18.3(13)	18.1(13)
s.d. (nm)	5.0(10)	4.9(10)	4.9(9)	4.5(3)
Specimen displ. (mm)	-0.011(6)	-0.203(6)	-0.025(4) (2004) -0.272(4) (2014)	-0.0075(4) <sup>a</sup>
WSS	2627	2739	5505	4506
GoF	1.01	1.03	1.04	1.78
Nfit	18	18	30	41
Nobs	2581	2581	2581	1463

<sup>a</sup>Error on the zero of the  $2\theta$  axis (in degrees).

displacement, zero error of the  $2\theta$  axis). However, this information is only subsidiary to the most relevant result concerning the line profiles, showing significant broadening from both domain size and microstrain effects. The latter, that was completely attributed to dislocations, treated according to the KW theory, corresponds to a high density of interacting dislocations; in fact, the low value of the Wilkens parameter ( $\text{Re} \cdot \sqrt{\rho}$ ) points out a strong interaction between dislocations, as in dipoles and wall structures. Values of this parameter, being all above unity, also confirm the results that are within the validity limits of the KW dislocation theory (Wilkens, 1970a, 1970b).

It is legitimate to doubt the reliability of LPA results when data comprise few peak profiles, as the  $hkl$ -dependent features might not be completely captured. The powder patterns discussed so far, collected using  $\text{CuK}\alpha$  radiation (Figures 2 and 3), include just six peaks of the  $bcc$  iron alloy. The same sample was then studied with the SR XRD, using a shorter wavelength (0.063 25 nm), such to include several additional peak profiles. Results, listed in the last column of Table I, agree closely with those from the laboratory XRD data, thus confirming the general validity of the WPPM procedure.

The reliability of the powder and the analysis technique is confirmed by the experimental evidence, which despite differences in the experimental setup (flat plate versus capillary sample holder; parafocusing Bragg–Brentano versus quasi-parallel beam Debye–Scherrer geometry; monochromatic versus two wavelength X-ray beams), shows remarkably similar results. It is however clear that, as expected, using SR provides results that are on an average more accurate than those from a laboratory source. Moreover, it is important to stress that the  $\text{CuK}\alpha$  wavelength ( $\lambda = 0.154$  18 nm) used in the laboratory equipment is very close to the  $K$ -edge absorption of the Fe contained in the sample ( $\lambda = 0.174$  33 nm), resulting in a limited penetration depth ( $\sim 5$   $\mu\text{m}$ ), affecting the signal intensity of the collected diffraction profile.

The extensive broadening (well beyond the breadth of the instrumental profile), with a substantial contribution of both size and microstrain effects, makes the specimen, ideal for microstructure studies. Coupled with a proven stability in time, this renders the powder as a good candidate for a reference material in LPA studies.

## IV. CONCLUSION

Extensive ball milling of a  $bcc$  iron-alloy powder yields an ideal candidate as a reference material for LPA. Plasticity effects are such to produce visible and easily measurable broadening of the diffraction peak profiles, caused both by the small size of the crystalline domains and by the strain attributable to lattice defects.

Unless deliberately exposed to highly oxidizing conditions, oxides phases are absent or present in little amount. The powder, in fact, tends to form relatively large agglomerates (tens of micrometers) of much finer crystalline domains; just as a thin passivation layer can form on the agglomerate surface, thus protecting the nanocrystalline domains from further oxidation. Stability was proved over a time range of 10 years.

## ACKNOWLEDGEMENTS

The authors thank Dr. Mirco D’Incau (University of Trento) for the preparation of the ball milled sample. The authors acknowledge the European Synchrotron Radiation Facility for the provision of synchrotron radiation facilities and they thank the staff of the ID31 (now ID22) beamline for assistance in data collection.

- Caglioti, G., Paoletti, A., and Ricci, F. P. (1958). “Choice of collimators for a crystal spectrofotometer for neutron diffraction,” *Nucl. Instrum.* **3**(4), 223–228.
- D’Incau, M., Leoni, M., and Scardi, P. (2007). “High-energy grinding of FeMo powders,” *J. Mater. Res.* **22**(6), 1744–1753.
- Dinnebier, R. E. and Billinge, S. J. L. (2008). *Powder Diffraction. Theory and Practice* (RSC Publishing, Cambridge, UK).
- Guinebreiere, R. (2007). *X-ray diffraction by Polycrystalline Materials* (Wiley-ISTE, London, UK).
- Klug, H. P. and Alexander, L. E. (1974). *X-ray Diffraction Procedures for Polycrystalline and Amorphous Materials* (Wiley, New York), 2nd ed.
- Krivoglaz, M. A. and Ryaboshapka, K. P. (1963). “Theory of X-ray scattering by crystals containing dislocations, screw and edge dislocations randomly distributed throughout the crystal,” *Fiz. Metall. Metalloved.* **15**, 18–31.
- Leoni, M., Confente, T., and Scardi, P. (2006). “PM2K: a flexible program implementing whole powder pattern modelling,” *Z. Kristallogr. Suppl.* **23**, 249–254.

- Martinez-Garcia, J., Leoni, M., and Scardi, P. (2009). "A general approach for determining the diffraction contrast factor of straight-line dislocations," *Acta Crystallogr. A* **65**, 109–119.
- Mittemeijer, E. J. and Scardi, P. (Eds.) (2004). *Diffraction Analysis of the Microstructure of Materials* (Springer series in Materials Science, Berlin, Germany).
- Scardi, P. and Leoni, M. (2002). "Whole powder pattern modelling," *Acta Crystallogr. A* **58**, 190–200.
- Scardi, P. and Leoni, M. (2006). "Line profile analysis: pattern modeling versus profile fitting," *J. Appl. Crystallogr.* **39**, 24–31.
- Scardi, P., Ortolani, M., and Leoni, M. (2010). "WPPM: microstructural analysis beyond the Rietveld method," *Mater. Sci. Forum* **651**, 155–171.
- Schwartz, L. H. and Cohen, J. B. (1977). *Diffraction from Materials* (Academic Press, New York).
- Snyder, R. L., Fiala, J., and Bunge, H. J. (Eds.) (2000). *Defect and Microstructure Analysis by Diffraction* (International Union of Crystallography; Oxford University Press).
- Staudemann, J. L., et al. (2000). *Certificate – Standard Reference Material 660a* (NIST, Gaithersburg, MD).
- Wilkens, M. (1970a). "Theoretical aspects of kinematical X-ray diffraction profiles from crystals containing dislocation distributions," In *Fundamental Aspects of Dislocation Theory*, edited by J. A. Simmons, de Wit, R. and Bullough, R. National Bureau of Standards (US) Special Publication No. 317 (National Bureau of Standards, Washington, DC), Vol. **II**, pp. 1195–1221.
- Wilkens, M. (1970b). "Determination of density and distribution of dislocations in deformed single crystals from broadened x-ray diffraction profiles," *Phys. Status Solidi A*, **2**, 359–370.